

**DICHIARAZIONE DI PRESTAZIONE**DoP N. **MKT-2.1-301\_it**

- ❖ **Codice di identificazione unico del prodotto-tipo:** **Sistema di iniezione VMU plus per calcestruzzo**
- ❖ **Usi previsti:** Ancorante incollato per ancoraggio nel calcestruzzo vedi allegato B /Annex B
- ❖ **Fabbricante:** MKT Metall-Kunststoff-Technik GmbH & Co.KG  
Auf dem Immel 2  
67685 Weilerbach
- ❖ **Sistemi di VVCP:** 1
- ❖ **Documento per la valutazione europea:** **EAD 330499-01-0601**  
Valutazione tecnica europea: **ETA-11/0415, 01.06.2021**  
Organismo di valutazione tecnica: DIBt, Berlin  
Organismi notificati: NB 2873 – Technische Universität Darmstadt

❖ **Prestazioni dichiarate:**

Caratteristiche essenziali	Prestazione
<b>Resistenza meccanica e stabilità (BWR 1)</b>	
Resistenze caratteristiche sotto carico di trazione (effetti statici e quasi statici)	Allegato/Annex B2, C1, C3, C4, C7, C9
Resistenze caratteristiche sotto stress trasversale (effetti statici e quasi statici)	Allegato/Annex C2, C5, C8, C10
Turni (effetti statici e quasi statici)	Allegato/Annex C12, C13
Resistenza caratteristica e turni per la categoria di prestazioni sismiche C1	Allegato/Annex C6, C11
Resistenza caratteristica e turni per la categoria di prestazioni sismiche C2	Prestazioni non valutate
<b>Igiene, salute e ambiente (BWR 3)</b>	
Contenuto, emissione e / o rilascio di sostanze pericolose	Prestazioni non valutate


La prestazione del prodotto sopra identificato è conforme all'insieme delle prestazioni dichiarate. La presente dichiarazione di responsabilità viene emessa, in conformità al regolamento (UE) n. 305/2011, sotto la sola responsabilità del fabbricante sopra identificato.

Firmato a nome e per conto del fabbricante da:



**Stefan Weustenhagen**  
(Direttore Generale)  
**Weilerbach, 01.06.2021**

p.p.



**Dipl.-Ing. Detlef Bigalke**  
(Direttore del Sviluppo del Prodotto)



L'originale di questa dichiarazione di prestazione è stata scritta in tedesco. In caso di deviazioni nella traduzione, la versione tedesca è valida.

## Specification of intended use

Injection System VMU plus	Threaded rod	Internally threaded anchor rod	Rebar
Static and quasi-static action	M8 - M30	IG-M6 - IG-M20 (zinc plated, A4, HCR)	Ø8 - Ø32
Seismic action, performance category C1	M8 - M30	-	Ø8 - Ø32
Base materials	compacted, reinforced or unreinforced normal weight concrete (without fibers), acc. to EN 206:2013 + A1:2016 strength classes C20/25 to C50/60 acc. to EN 206-1:2013+A1:2016 cracked and uncracked concrete		
Temperature Range I -40°C to +40°C	max long term temperature +24 °C and max short term temperature +40°C		
Temperature Range II -40°C to +80°C	max long term temperature +50 °C and max short term temperature +80°C		
Temperature Range III -40°C to 120°C	max long term temperature +72 °C and max short term temperature +120°C		

### Use conditions (Environmental conditions):

- Structures subject to dry internal conditions (all materials).
- For all other conditions:  
Intended use of Material according to Annx A4, Table A1 corresponding corrosion resistance classes CRC according to EN 1993-1-4:2006 +A1:2015

### Design:

- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the anchor is indicated on the design drawings (e. g. position of the anchor relative to reinforcement or to supports, etc.)
- Anchorages are designed under the responsibility of an engineer experienced in anchorages and concrete work
- Anchorages are designed in accordance with EN 1992-4:2018 and Technical Report TR 055, Edition February 2018

### Installation:

- Dry or wet concrete: M8 to M30, IG-M6 to IG-M20, Rebar Ø8 to Ø32
- Waterfilled holes (not sea water): M8 to M16, IG-M6 to IG-M10, Rebar Ø8 to Ø16
- Hole drilling by hammer or compressed air drill mode or vacuum drill mode
- Installation direction D3: downwards, horizontally and upwards (overhead) installation
- Anchor installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site
- The injection mortar is assessed for installation at minimum concrete temperature of -10°C resp. -20°C, where subsequently the temperature in the concrete does not rise at a rapid rate, i.e. from the minimum installation temperature to 24°C within a 12-hour period.
- Internally threaded anchor rod: screws and threaded rods (incl. nut and washer) must at least correspond to the material and strength class of the internally threaded anchor rod used

## Injection system VMU plus for concrete

Intended Use  
Specifications

**Annex B1**

**Table B1: Installation parameters for threaded rod**

Threaded rod			M8	M10	M12	M16	M20	M24	M27	M30
Diameter threaded rod	$d=d_{nom}$	[mm]	8	10	12	16	20	24	27	30
Nominal drill hole diameter	$d_0$	[mm]	10	12	14	18	24	28	32	35
Effective anchorage depth	$h_{ef,min}$	[mm]	60	60	70	80	90	96	108	120
	$h_{ef,max}$	[mm]	160	200	240	320	400	480	540	600
Diameter of clearance hole in the fixture	Pre-setting installation $d_f \leq$	[mm]	9	12	14	18	22	26	30	33
	Through setting installation $d_f \leq$	[mm]	12	14	16	20	25	30	33	38
Installation torque	$\max T_{inst} \leq$	[Nm]	10	20	40 (35) <sup>1)</sup>	80	120	160	180	200
Minimum thickness of member	$h_{min}$	[mm]	$h_{ef} + 30mm \geq 100mm$			$h_{ef} + 2d_0$				
Minimum spacing	$s_{min}$	[mm]	40	50	60	80	100	120	135	150
Minimum edge distance	$c_{min}$	[mm]	40	50	60	80	100	120	135	150

<sup>1)</sup> max. installation torque for property class 4.6

**Table B2: Installation parameters for internally threaded anchor rod**

Internally threaded anchor rod			IG-M 6	IG-M 8	IG-M 10	IG-M 12	IG-M 16	IG-M 20
Inner diameter of threaded rod	$d_2$	[mm]	6	8	10	12	16	20
Outer diameter of threaded rod <sup>1)</sup>	$d=d_{nom}$	[mm]	10	12	16	20	24	30
Nominal drill hole diameter	$d_0$	[mm]	12	14	18	24	28	35
Effective anchorage depth	$h_{ef,min}$	[mm]	60	70	80	90	96	120
	$h_{ef,max}$	[mm]	200	240	320	400	480	600
Diameter of clearance hole in the fixture	$d_f \leq$	[mm]	7	9	12	14	18	22
Installation torque	$\max T_{inst} \leq$	[Nm]	10	10	20	40	60	100
Minimum screw-in depth	$l_{IG}$	[mm]	8	8	10	12	16	20
Minimum thickness of member	$h_{min}$	[mm]	$h_{ef} + 30 \text{ mm} \geq 100 \text{ mm}$			$h_{ef} + 2d_0$		
Minimum spacing	$s_{min}$	[mm]	50	60	80	100	120	150
Minimum edge distance	$c_{min}$	[mm]	50	60	80	100	120	150

<sup>1)</sup> with metric thread acc. to EN 1993-1-8:2005+AC:2009

**Table B3: Installation parameters for rebar**










Rebar			Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 25	Ø 28	Ø 32
Diameter threaded rod	$d=d_{nom}$	[mm]	8	10	12	14	16	20	24	28	32
Nominal drill hole diameter	$d_0$	[mm]	12	14	16	18	20	24	32	35	40
Effective anchorage depth	$h_{ef,min}$	[mm]	60	60	70	75	80	90	100	112	128
	$h_{ef,max}$	[mm]	160	200	240	280	320	400	500	560	640
Minimum thickness of member	$h_{min}$	[mm]	$h_{ef} + 30 \text{ mm} \geq 100 \text{ mm}$			$h_{ef} + 2d_0$					
Minimum spacing	$s_{min}$	[mm]	40	50	60	70	80	100	125	140	160
Minimum edge distance	$c_{min}$	[mm]	40	50	60	70	80	100	125	140	160

**Injection system VMU plus for concrete**

**Intended Use**  
Installation parameters

**Annex B2**

**Table B4: Parameter cleaning and setting tools**

Threaded rod	Internally threaded anchor rod	Rebar	Drill bit $\varnothing$	Brush $\varnothing$	min. Brush $\varnothing$	Retaining washer			
						<b>Installation direction and use of retaining washer</b>			
[-]	[-]	$\varnothing$ [mm]	$d_0$ [mm]	$d_b$ [mm]	$d_{b,min}$ [mm]	[-]			
M8			10	12	10,5	No retaining washer required			
M10	VMU-IG M 6	8	12	14	12,5				
M12	VMU-IG M 8	10	14	16	14,5				
		12	16	18	16,5				
M16	VMU-IG M10	14	18	20	18,5	VM-IA 18	$h_{ef} > 250\text{mm}$	$h_{ef} > 250\text{mm}$	all
		16	20	22	20,5	VM-IA 20			
M20	VMU-IG M12	20	24	26	24,5	VM-IA 24			
M24	VMU-IG M16		28	30	28,5	VM-IA 28			
M27		25	32	34	32,5	VM-IA 32			
M30	VMU-IG M20	28	35	37	35,5	VM-IA 35			
		32	40	41,5	40,5	VM-IA 40			



**Blow-out pump (volume 750ml)**  
 Drill bit diameter ( $d_0$ ): 10 mm to 20 mm  
 Anchorage depth ( $h_{ef}$ ):  $\leq 10 d_{nom}$   
 for uncracked concrete



**Recommended compressed air tool (min 6 bar)**  
 All applications



**Retaining washer for overhead or horizontal installation**  
 Drill bit diameter ( $d_0$ ):  
 18 mm to 40 mm



**Steel brush**  
 Drill bit diameter ( $d_0$ ): all diameters

**Injection system VMU plus for concrete**

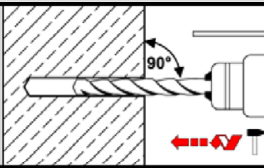
**Intended Use**  
 Cleaning and setting tools

**Annex B3**

# Installation instructions

## Drilling of the hole

1



Drill the hole by applying the drilling method acc. to Annex B1, the drill bit diameter (Table B4) and the selected drill hole depth.  
In case of aborted hole, the drill hole shall be filled with mortar


## Cleaning, all drilling methods

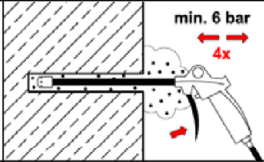**Attention! Standing water in the drill hole must be removed before cleaning!**

### Cleaning with compressed air


(all diameters, cracked and uncracked concrete)

2a




Starting from the bottom or back of the drill hole, blow out the hole with compressed air (min. 6 bar) **four** times, until return air stream is free of noticeable dust.  
If the drill hole ground is not reached, an extension must be used.

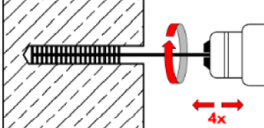2b



Brush the hole with an appropriate sized wire brush  $> d_{b,min}$  (Table B4) **four** times.  
If the drill hole ground is not reached, a brush extension shall be used.

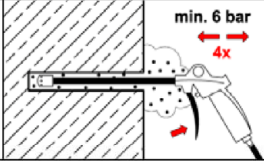2c



Finally blow the hole clean again with compressed air (min. 6 bar) **four** times, until the outgoing airstream is free of dust. If the drill hole ground is not reached an extension shall be used.

2

### Manual cleaning

uncracked concrete: Drill hole diameter  $d_0 \leq 20\text{mm}$  and effective anchorage depth  $h_{ef} \leq 10 d_{nom}$

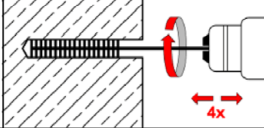
cracked concrete: Drill hole diameter:  $14\text{mm} \leq d_0 \leq 20\text{mm}$  and effective anchorage depth  $h_{ef} \leq 10 d_{nom}$

2a




Starting from the bottom or back of the drill hole, blow the hole clean with the blow-out pump **four** times until return air stream is free of noticeable dust.

2b



Brush the hole **four** times with an appropriate sized wire brush  $> d_{b,min}$  (Table B4).  
If the drill hole ground is not reached, a brush extension shall be used.

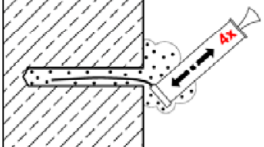2c



Finally blow the hole clean again with the blow-out pump **four** times until return air stream is free of noticeable dust.






**After cleaning, the drill hole has to be protected against re-contamination in an appropriate way, until dispensing the mortar in the drill hole. If necessary, the cleaning has to be repeated directly before dispensing the mortar. In-flowing water must not contaminate the drill hole again.**
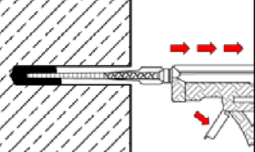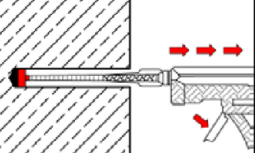
## Injection system VMU plus for concrete

**Intended Use**  
Installation instructions

**Annex B4**

## Installation instructions (continuation)

Injection		
3		Attach a supplied static-mixing nozzle to the cartridge and load the cartridge into the correct dispensing tool. For every working interruption longer than the recommended working time (Table B5 or Table B6) as well as for new cartridges, a new static-mixer shall be used.
4		Before injecting the mortar, mark the required anchorage depth on the fastening element.
5		Prior to dispensing into the drill hole, squeeze out separately a minimum of three full strokes and discard non-uniformly mixed adhesive components until the mortar shows a consistent grey colour. For tubular film cartridges dismiss a minimum of six full strokes.
6a		Starting from the bottom or back of the cleaned drill hole fill the hole up to approximately two-thirds with adhesive. Slowly withdraw the static mixing nozzle as the hole fills to avoid air pockets. For embedment larger than 190mm an extension nozzle shall be used. Observe the gel-/ working times given in Table B5 or Table B6.
6b		Retaining washer and mixer nozzle extensions shall be used according to Annex B3 for the following applications: <ul style="list-style-type: none"> <li>• Horizontal installation (horizontal direction) and ground installation (vertical downwards direction): Drill bit-<math>\varnothing</math> <math>d_0 \geq 18</math> mm and embedment depth <math>h_{ef} &gt; 250</math>mm</li> <li>• Overhead installation: Drill bit-<math>\varnothing</math> <math>d_0 \geq 18</math> mm</li> </ul>

Injection system VMU plus for concrete







**Intended Use**  
Installation instructions (continuation)

**Annex B5**


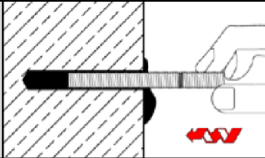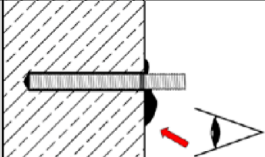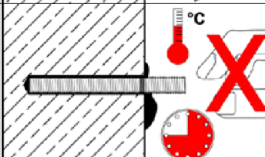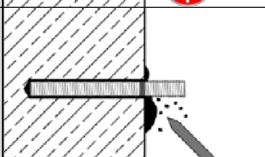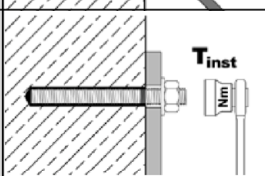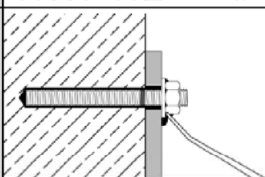
## Installation instructions (continuation)

### Setting the fastening element

7		<p>Push fastening element into the hole while turning slightly to ensure proper distribution of the adhesive until the embedment depth is reached. The anchor shall be free of dirt, grease, oil or other foreign material.</p>
8		<p>Make sure that the fastening element is fully seated up to the full embedment depth and that excess mortar is visible at the top of the hole. If these requirements are not maintained, the application has to be renewed before the end of the working time. For overhead installation, the anchor should be fixed (e.g. by wedges).</p>
9		<p>Allow the adhesive to cure to the specified time prior to applying any load or torque. Do not move or load the anchor until it is fully cured (Table B5 or Table B6).</p>
10		<p>Remove excess mortar.</p>
11		<p>The fixture can be mounted after curing time. Apply installation torque <math>\leq T_{inst}</math> according to Table B1 or B2.</p>
12		<p>Optionally, for pre-setting installation, the annular gap between anchor rod and attachment can be filled with mortar. Therefore replace the regular washer by washer with drill and plug on reducing adapter on static mixer. Annular gap is completely filled, when excess mortar seeps out.</p>

Injection system VMU plus for concrete

**Intended Use**  
Installation instructions (continuation)

**Annex B6**

**Table B5: Maximum processing time and minimum curing time, VMU plus**

Concrete temperature	Maximum processing time	Minimum curing time in dry concrete <sup>1)</sup>
- 10°C to - 6°C	90 min <sup>2)</sup>	24 h <sup>2)</sup>
- 5°C to - 1°C	90 min	14 h
0°C to + 4°C	45 min	7 h
+ 5°C to + 9°C	25 min	2 h
+ 10°C to + 19°C	15 min	80 min
+ 20°C to + 29°C	6 min	45 min
+ 30°C to + 34°C	4 min	25 min
+ 35°C to + 39°C	2 min	20 min
+ 40°C	1,5 min	15 min
<b>Cartridge temperature</b>	<b>+ 5°C to + 40°C</b>	

<sup>1)</sup> in wet concrete the curing time must be doubled

<sup>2)</sup> cartridge temperature must be at min. +15°C

**Table B6: Maximum processing time and minimum curing time, VMU plus Polar**

Concrete temperature	Maximum processing time	Minimum curing time in dry concrete <sup>1)</sup>
- 20°C to - 16°C	75 min	24 h
- 15°C to - 11°C	55 min	16 h
- 10°C to - 6°C	35 min	10 h
- 5°C to - 1°C	20 min	5 h
0°C to + 4°C	10 min	2,5 h
+ 5°C to + 9°C	6 min	80 min
+10°C	6 min	60 min
<b>Cartridge temperature</b>	<b>- 20°C to + 10°C</b>	

<sup>1)</sup> in wet concrete the curing time must be doubled

**Injection system VMU plus for concrete**

**Intended Use**  
Processing time and curing time

**Annex B7**



**Table C1: Characteristic steel resistances for threaded rods under tension loads**

Threaded rod				M8	M10	M12	M16	M20	M24	M27	M30
<b>Steel failure</b>											
Cross sectional area $A_s$ [mm <sup>2</sup> ]				36,6	58,0	84,3	157	245	353	459	561
<b>Characteristic resistance under tension load <sup>1)</sup></b>											
Steel, zinc plated	Property class 4.6 and 4.8	$N_{Rk,s}$	[kN]	15 (13)	23 (21)	34	63	98	141	184	224
	Property class 5.6 and 5.8	$N_{Rk,s}$	[kN]	18 (17)	29 (27)	42	78	122	176	230	280
	Property class 8.8	$N_{Rk,s}$	[kN]	29 (27)	46 (43)	67	125	196	282	368	449
Stainless steel	A2, A4 and HCR Property class 50	$N_{Rk,s}$	[kN]	18	29	42	79	123	177	230	281
	A2, A4 and HCR Property class 70	$N_{Rk,s}$	[kN]	26	41	59	110	171	247	_ <sup>3)</sup>	_ <sup>3)</sup>
	A4 and HCR Property class 80	$N_{Rk,s}$	[kN]	29	46	67	126	196	282	_ <sup>3)</sup>	_ <sup>3)</sup>
<b>Partial factors <sup>2)</sup></b>											
Steel, zinc plated	Property class 4.6	$\gamma_{Ms,N}$	[-]	2,0							
	Property class 4.8	$\gamma_{Ms,N}$	[-]	1,5							
	Property class 5.6	$\gamma_{Ms,N}$	[-]	2,0							
	Property class 5.8	$\gamma_{Ms,N}$	[-]	1,5							
	Property class 8.8	$\gamma_{Ms,N}$	[-]	1,5							
Stainless steel	A2, A4 and HCR Property class 50	$\gamma_{Ms,N}$	[-]	2,86							
	A2, A4 and HCR Property class 70	$\gamma_{Ms,N}$	[-]	1,87						_ <sup>3)</sup>	_ <sup>3)</sup>
	A4 and HCR Property class 80	$\gamma_{Ms,N}$	[-]	1,6						_ <sup>3)</sup>	_ <sup>3)</sup>

<sup>1)</sup> the characteristic resistances apply for all anchor rods with the cross sectional area  $A_s$  specified here: VMU-A, V-A, VM-A  
For commercial standard threaded rods with a smaller cross sectional area (e.g. hot-dip galvanized threaded rods M8, M10 according to EN ISO 10684:2004 + AC:2009), the values in brackets are valid.

<sup>2)</sup> in absence of national regulation

<sup>3)</sup> Anchor type not part of the ETA

**Injection system VMU plus for concrete**

**Performance**

Characteristic steel resistances for **threaded rods** under **tension loads**

**Annex C1**

**Table C2: Characteristic steel resistances for threaded rods under shear loads**

Threaded rod				M8	M10	M12	M16	M20	M24	M27	M30
<b>Steel failure</b>											
Cross sectional area $A_s$ [mm <sup>2</sup> ]				36,6	58,0	84,3	157	245	353	459	561
<b>Characteristic resistance under shear load <sup>1)</sup></b>											
<b>Steel failure <u>without</u> lever arm</b>											
Steel, zinc plated	Property class 4.6 and 4.8	$V^{0}_{Rk,s}$ [kN]	9 (8)	14 (13)	20	38	59	85	110	135	
	Property class 5.6 and 5.8	$V^{0}_{Rk,s}$ [kN]	11 (10)	17 (16)	25	47	74	106	138	168	
	Property class 8.8	$V^{0}_{Rk,s}$ [kN]	15 (13)	23 (21)	34	63	98	141	184	224	
Stainless steel	A2, A4 and HCR, property class 50	$V^{0}_{Rk,s}$ [kN]	9	15	21	39	61	88	115	140	
	A2, A4 and HCR, property class 70	$V^{0}_{Rk,s}$ [kN]	13	20	30	55	86	124	.. <sup>3)</sup>	.. <sup>3)</sup>	
	A4 and HCR, property class 80	$V^{0}_{Rk,s}$ [kN]	15	23	34	63	98	141	.. <sup>3)</sup>	.. <sup>3)</sup>	
<b>Steel failure <u>with</u> lever arm</b>											
Steel, zinc plated	Property class 4.6 and 4.8	$M^{0}_{Rk,s}$ [Nm]	15 (13)	30 (27)	52	133	260	449	666	900	
	Property class 5.6 and 5.8	$M^{0}_{Rk,s}$ [Nm]	19 (16)	37 (33)	65	166	324	560	833	1123	
	Property class 8.8	$M^{0}_{Rk,s}$ [Nm]	30 (26)	60 (53)	105	266	519	896	1333	1797	
Stainless steel	A2, A4 and HCR, property class 50	$M^{0}_{Rk,s}$ [Nm]	19	37	66	167	325	561	832	1125	
	A2, A4 and HCR, property class 70	$M^{0}_{Rk,s}$ [Nm]	26	52	92	232	454	784	.. <sup>3)</sup>	.. <sup>3)</sup>	
	A4 and HCR, property class 80	$M^{0}_{Rk,s}$ [Nm]	30	59	105	266	519	896	.. <sup>3)</sup>	.. <sup>3)</sup>	
<b>Partial factor <sup>2)</sup></b>											
Steel, zinc plated	Property class 4.6	$\gamma_{Ms,V}$ [-]	1,67								
	Property class 4.8	$\gamma_{Ms,V}$ [-]	1,25								
	Property class 5.6	$\gamma_{Ms,V}$ [-]	1,67								
	Property class 5.8	$\gamma_{Ms,V}$ [-]	1,25								
	Property class 8.8	$\gamma_{Ms,V}$ [-]	1,25								
Stainless steel	A2, A4 and HCR, property class 50	$\gamma_{Ms,V}$ [-]	2,38								
	A2, A4 and HCR, property class 70	$\gamma_{Ms,V}$ [-]	1,56						.. <sup>3)</sup>	.. <sup>3)</sup>	
	A4 and HCR, property class 80	$\gamma_{Ms,V}$ [-]	1,33						.. <sup>3)</sup>	.. <sup>3)</sup>	

1) the characteristic resistances apply for all anchor rods with the cross sectional area  $A_s$  specified here: VMU-A, V-A, VM-A  
For commercial standard threaded rods with a smaller cross sectional area (e.g. hot-dip galvanized threaded rods M8, M10 according to EN ISO 10684:2004 + AC:2009), the values in brackets are valid.

2) in absence of national regulation

3) Anchor type not part of the ETA

**Injection system VMU plus for concrete**

**Performance**

Characteristic steel resistances for **threaded rods** under **tension loads**

**Annex C2**

**Table C3: Characteristic values for concrete cone and splitting failure**

Threaded rods / Internally threaded anchor rods / Rebars				all sizes
<b>Concrete cone failure</b>				
Factor $k_1$	uncracked concrete	$k_{Ucr,N}$	[-]	11,0
	cracked concrete	$k_{Cr,N}$	[-]	7,7
Edge distance		$C_{Cr,N}$	[mm]	$1,5 \cdot h_{ef}$
Spacing		$S_{Cr,N}$	[mm]	$2 \cdot C_{Cr,N}$
<b>Splitting failure</b>				
Characteristic resistance		$N^0_{Rk,sp}$	[kN]	$\min ( N_{Rk,p} ; N^0_{Rk,c} )$
Edge distance	$h/h_{ef} \geq 2,0$	$C_{Cr,sp}$	[mm]	$1,0 \cdot h_{ef}$
	$2,0 > h/h_{ef} > 1,3$			$2 \cdot h_{ef} (2,5 - h / h_{ef})$
	$h/h_{ef} \leq 1,3$			$2,4 \cdot h_{ef}$
Spacing		$S_{Cr,sp}$	[mm]	$2 \cdot C_{Cr,sp}$

**Injection system VMU plus for concrete**

**Performance**  
 Characteristic values for **concrete cone** and **splitting failure**

**Annex C3**

**Table C4: Characteristic values for threaded rods under tension loads**

Threaded rod			M8	M10	M12	M16	M20	M24	M27	M30		
<b>Steel failure</b>												
Characteristic resistance			$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}$ (or see Table C1)							
Partial factor			$\gamma_{Ms,N}$	[-]	see Table C1							
<b>Combined pull-out and concrete failure</b>												
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>												
Temperature range	I: 40°C/24°C	dry or wet concrete	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	10	12	12	12	12	11	10	9
	II: 80°C/50°C				7,5	9	9	9	9	8,5	7,5	6,5
	III: 120°C/72°C				5,5	6,5	6,5	6,5	6,5	6,5	5,5	5,0
	I: 40°C/24°C	waterfilled drill hole	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	7,5	8,5	8,5	8,5	no performance assessed			
	II: 80°C/50°C				5,5	6,5	6,5	6,5				
	III: 120°C/72°C				4,0	5,0	5,0	5,0				
<b>Characteristic bond resistance in <u>cracked</u> concrete C20/25</b>												
Temperature range	I: 40°C/24°C	dry or wet concrete	$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	4,0	5,0	5,5	5,5	5,5	5,5	6,5	6,5
	II: 80°C/50°C				2,5	3,5	4,0	4,0	4,0	4,0	4,5	4,5
	III: 120°C/72°C				2,0	2,5	3,0	3,0	3,0	3,0	3,5	3,5
	I: 40°C/24°C	waterfilled drill hole	$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	4,0	4,0	5,5	5,5	no performance assessed			
	II: 80°C/50°C				2,5	3,0	4,0	4,0				
	III: 120°C/72°C				2,0	2,5	3,0	3,0				
<b>Reduction factor <math>\psi^0_{sus}</math> in concrete C20/25</b>												
Temperature range	I: 40°C/24°C	dry or wet concrete; waterfilled drill hole	$\psi^0_{sus}$	[-]	0,73							
	II: 80°C/50°C				0,65							
	III: 120°C/72°C				0,57							
Increasing factors for $\tau_{Rk}$			$\psi_c$	[-]	C25/30						1,02	
					C30/37						1,04	
					C35/45						1,07	
					C40/50						1,08	
					C45/55						1,09	
					C50/60						1,10	
<b>Concrete cone failure</b>												
Relevant parameter			see Table C3									
<b>Splitting failure</b>												
Relevant parameter			see Table C3									
<b>Installation factor</b>												
dry or wet concrete			$\gamma_{inst}$	[-]	1,0	1,2						
waterfilled drill hole			$\gamma_{inst}$	[-]	1,4			no performance assessed				

**Injection system VMU plus for concrete**

**Performance**  
Characteristic values for **threaded rods** under **tension loads**

**Annex C4**

**Table C5: Characteristic values for threaded rods under shear loads**

Threaded rod			M8	M10	M12	M16	M20	M24	M27	M30
<b>Steel failure without lever arm</b>										
Characteristic resistance, steel zinc plated, property class 4.6, 4.8, 5.6, 5.8	$V_{Rk,s}^0$	[kN]	0,6 · A <sub>s</sub> · f <sub>uk</sub> (or see table C2)							
Characteristic resistance, steel zinc plated, property class 8.8, stainless steel A2 / A4 / HCR, all property classes	$V_{Rk,s}^0$	[kN]	0,5 · A <sub>s</sub> · f <sub>uk</sub> (or see table C2)							
Ductility factor	k <sub>7</sub>	[-]	1,0							
Partial factor	γ <sub>Ms,V</sub>	[-]	see Table C2							
<b>Steel failure with lever arm</b>										
Characteristic bending moment	$M_{Rk,s}^0$	[Nm]	1,2 · W <sub>el</sub> · f <sub>uk</sub> (or see table C2)							
Elastic section modulus	W <sub>el</sub>	[mm <sup>3</sup> ]	31	62	109	277	541	935	1387	1874
Partial factor	γ <sub>Ms,V</sub>	[-]	see table C2							
<b>Concrete pry-out failure</b>										
Pry-out Factor	k <sub>8</sub>	[-]	2,0							
<b>Concrete edge failure</b>										
Effective length of anchor	l <sub>f</sub>	[mm]	min(h <sub>ef</sub> ; 12 d <sub>nom</sub> )						min(h <sub>ef</sub> ; 300mm)	
Outside diameter of anchor	d <sub>nom</sub>	[mm]	8	10	12	16	20	24	27	30
Installation factor	γ <sub>inst</sub>	[-]	1,0							

**Injection system VMU plus for concrete**

**Performance**  
 Characteristic value for **threaded rods** under **shear loads**

**Annex C5**

**Table C6: Characteristic values for threaded rods under tension load, seismic action, performance category C1**

Threaded rod				M8	M10	M12	M16	M20	M24	M27	M30	
<b>Steel failure</b>												
Characteristic resistance		$N_{Rk,s,C1}$	[kN]	$1,0 \cdot N_{Rk,s}$								
Partial factor		$\gamma_{Ms,V}$	[-]	see Table C1								
<b>Combined pull-out and concrete failure</b>												
<b>Characteristic bond resistance in concrete C20/25 to C50/60</b>												
Temperature range	I: 40°C/24°C	dry or wet concrete	$\tau_{Rk,C1}$	[N/mm <sup>2</sup> ]	2,5	3,1	3,7	3,7	3,7	3,8	4,5	4,5
	II: 80°C/50°C				1,6	2,2	2,7	2,7	2,7	2,8	3,1	3,1
	III: 120°C/72°C				1,3	1,6	2,0	2,0	2,0	2,1	2,4	2,4
	I: 40°C/24°C	waterfilled drill hole	$\tau_{Rk,C1}$	[N/mm <sup>2</sup> ]	2,5	2,5	3,7	3,7	no performance assessed			
	II: 80°C/50°C				1,6	1,9	2,7	2,7				
	III: 120°C/72°C				1,3	1,6	2,0	2,0				
<b>Installation factor</b>												
Dry or wet concrete		$\gamma_{inst}$	[-]	1,0	1,2							
Waterfilled drill hole		$\gamma_{inst}$	[-]	1,4					no performance assessed			

**Table C7: Characteristic values for threaded rods under shear load, seismic action, performance category C1**

Threaded rod				M8	M10	M12	M16	M20	M24	M27	M30
<b>Steel failure</b>											
Characteristic resistance		$V_{Rk,s,C1}$	[kN]	$0,7 \cdot V^0_{Rk,s}$							
Partial factor		$\gamma_{Ms,V}$	[-]	See Table C2							
<b>Factor for annular gap</b>											
Factor for anchorages	without hole clearance	$\alpha_{gap}$	[-]	1,0							
	with hole clearance between fastener and fixture	$\alpha_{gap}$	[-]	0,5							

**Injection system VMU plus for concrete**

**Performance**  
Characteristic values for **threaded rods** under **seismic action**, category **C1**

**Annex C6**



**Table C8: Characteristic values of tension loads for internally threaded anchor rods**

Internally threaded anchor rod				IG-M 6	IG-M 8	IG-M 10	IG-M 12	IG-M 16	IG-M 20	
<b>Steel failure <sup>1)</sup></b>										
Characteristic resistance, steel zinc plated, strength class	5.8	$N_{Rk,s}$	[kN]	10	17	29	42	76	123	
	8.8	$N_{Rk,s}$	[kN]	16	27	46	67	121	196	
Partial factor		$\gamma_{Ms,N}$	[-]	1,5						
Characteristic resistance, stainless steel A4 / HCR, strength class 70		$N_{Rk,s}$	[kN]	14	26	41	59	110	124 <sup>2)</sup>	
Partial factor		$\gamma_{Ms,N}$	[-]	1,87					2,86	
<b>Combined pull-out and concrete cone failure</b>										
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>										
Temperature range	I: 40°C/24°C	dry and wet concrete	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	12	12	12	12	11	9,0
	II: 80°C/50°C			[N/mm <sup>2</sup> ]	9,0	9,0	9,0	9,0	8,5	6,5
	III: 120°C/72°C			[N/mm <sup>2</sup> ]	6,5	6,5	6,5	6,5	6,5	5,0
	I: 40°C/24°C	waterfilled drill hole	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	8,5	8,5	8,5	no performance assessed		
	II: 80°C/50°C			[N/mm <sup>2</sup> ]	6,5	6,5	6,5			
	III: 120°C/72°C			[N/mm <sup>2</sup> ]	5,0	5,0	5,0			
<b>Characteristic bond resistance in <u>cracked</u> concrete C20/25</b>										
Temperature range	I: 40°C/24°C	dry and wet concrete	$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	5,0	5,5	5,5	5,5	5,5	6,5
	II: 80°C/50°C			[N/mm <sup>2</sup> ]	3,5	4,0	4,0	4,0	4,0	4,5
	III: 120°C/72°C			[N/mm <sup>2</sup> ]	2,5	3,0	3,0	3,0	3,0	3,5
	I: 40°C/24°C	waterfilled drill hole	$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	4,0	5,5	5,5	no performance assessed		
	II: 80°C/50°C			[N/mm <sup>2</sup> ]	3,0	4,0	4,0			
	III: 120°C/72°C			[N/mm <sup>2</sup> ]	2,5	3,0	3,0			
<b>Reductionfactor <math>\psi^0_{sus}</math> in concrete C20/25</b>										
Temperature range	I: 40°C/24°C	dry and wet concrete	$\psi^0_{sus}$	[-]	0,73					
	II: 80°C/50°C				0,65					
	III: 120°C/72°C				0,57					
Increasing factors for $\tau_{Rk}$				$\psi_c$	C25/30	1,02				
					C30/37	1,04				
					C35/45	1,07				
					C40/50	1,08				
					C45/55	1,09				
					C50/60	1,10				
<b>Concrete cone failure and splitting failure</b>										
Relevant parameter				see Table C3						
<b>Installation factor</b>										
dry and wet concrete		$\gamma_{inst}$	[-]	1,2						
waterfilled drill hole		$\gamma_{inst}$	[-]	1,4			no performance determined			

<sup>1)</sup> fastening screws or threaded rods (incl. nut and washer) must comply with the appropriate material and property class of the internally threaded anchor rod. The characteristic tension resistance for steel failure of the given strength class are valid for the internally threaded anchor rod and the fastening element.

<sup>2)</sup> for VMU-IG M20: Internally threaded rod: strength class 50; Fastening screws or threaded rods (incl. nut and washer): strength class 70

**Injection system VMU plus for concrete**

**Performance**

Characteristic values for **internally threaded anchor rods** under **tension loads**

**Annex C7**

**Table C9: Characteristic values for internally threaded anchor rods under shear loads**

Internally threaded anchor rod				IG-M 6	IG-M 8	IG-M 10	IG-M 12	IG-M 16	IG-M 20
<b>Steel failure <u>without</u> lever arm<sup>1)</sup></b>									
Characteristic resistance, steel zinc plated, strength class	5.8	$V_{Rk,s}^0$	[kN]	6	10	17	25	45	74
	8.8	$V_{Rk,s}^0$	[kN]	8	14	23	34	60	98
Partial factor		$\gamma_{Ms,V}$	[-]	1,25					
Characteristic resistance, stainless steel A4 / HCR, strength class	70	$V_{Rk,s}^0$	[kN]	7	13	20	30	55	62 <sup>2)</sup>
		$\gamma_{Ms,V}$	[-]	1,56					2,38
Ductility factor		$k_7$	[-]	1,0					
<b>Steel failure <u>with</u> lever arm<sup>1)</sup></b>									
Characteristic bending moment, steel zinc plated, strength class	5.8	$M_{Rk,s}^0$	[Nm]	8	19	37	66	167	325
	8.8	$M_{Rk,s}^0$	[Nm]	12	30	60	105	267	519
Partial factor		$\gamma_{Ms,V}$	[-]	1,25					
Characteristic bending resistance, stainless steel A4 / HCR, strength class	70	$M_{Rk,s}^0$	[Nm]	11	26	53	92	234	643 <sup>2)</sup>
		$\gamma_{Ms,V}$	[-]	1,56					2,38
<b>Concrete pry-out failure</b>									
Pry-out factor		$k_8$	[-]	2,0					
<b>Concrete edge failure</b>									
Effective length of anchor		$l_f$	[mm]	min( $h_{ef}$ ; 12 $d_{nom}$ )					min ( $h_{ef}$ ; 300mm)
Outside diameter of anchor		$d_{nom}$	[mm]	10	12	16	20	24	30
Installation factor		$\gamma_{inst}$	[-]	1,0					

<sup>1)</sup> fastening screws or threaded rods (incl. nut and washer) must comply with the appropriate material and property class of the internally threaded anchor rod. The characteristic shear resistance for steel failure of the given strength class are valid for the internally threaded anchor rod and the fastening element

<sup>2)</sup> for VMU-IG M20: Internally threaded rod: strength class 50; Fastening screws or threaded rods (incl. nut and washer): strength class 70

**Injection system VMU plus for concrete**

**Performance**  
 Characteristic values for **internally threaded anchor rods** under **shear loads**

**Annex C8**

**Table C10: Characteristic values for rebar under tension loads**

Rebar			Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 25	Ø 28	Ø 32		
<b>Steel failure</b>													
Characteristic resistance	$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}^{1)}$										
Cross sectional area	$A_s$	[mm <sup>2</sup> ]	50	79	113	154	201	314	491	616	804		
Partial factor	$\gamma_{Ms,N}$	[-]	1,4 <sup>2)</sup>										
<b>Combined pull-out and concrete cone failure</b>													
<b>Characteristic bond resistance in uncracked concrete C20/25</b>													
Temperature range	I: 40°C/24°C	dry and wet concrete	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	10	12	12	12	12	12	11	10	8,5
	II: 80°C/50°C				7,5	9,0	9,0	9,0	9,0	9,0	8,0	7,0	6,0
	III: 120°C/72°C				5,5	6,5	6,5	6,5	6,5	6,5	6,0	5,0	4,5
	I: 40°C/24°C	waterfilled drill hole	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	7,5	8,5	8,5	8,5	8,5	no performance assessed			
	II: 80°C/50°C				5,5	6,5	6,5	6,5	6,5				
	III: 120°C/72°C				4,0	5,0	5,0	5,0	5,0				
<b>Characteristic bond resistance in cracked concrete C20/25</b>													
Temperature range	I: 40°C/24°C	dry and wet concrete	$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	4,0	5,0	5,5	5,5	5,5	5,5	5,5	6,5	6,5
	II: 80°C/50°C				2,5	3,5	4,0	4,0	4,0	4,0	4,0	4,5	4,5
	III: 120°C/72°C				2,0	2,5	3,0	3,0	3,0	3,0	3,0	3,5	3,5
	I: 40°C/24°C	waterfilled drill hole	$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	4,0	4,0	5,5	5,5	5,5	no performance assessed			
	II: 80°C/50°C				2,5	3,0	4,0	4,0	4,0				
	III: 120°C/72°C				2,0	2,5	3,0	3,0	3,0				
<b>Reductionfactor <math>\psi_{sus}^0</math> in concrete C20/25</b>													
Temperature range	I: 40°C/24°C	dry and wet concrete	$\psi_{sus}^0$	[-]	0,73								
	II: 80°C/50°C				0,65								
	III: 120°C/72°C				0,57								
Increasing factors for $\tau_{Rk}$			$\psi_c$	[-]	C25/30							1,02	
					C30/37							1,04	
					C35/45							1,07	
					C40/50							1,08	
					C45/55							1,09	
					C50/60							1,10	
<b>Concrete cone failure and splitting failure</b>													
Relevant parameter			see Table C3										
<b>Installation factor</b>													
dry and wet concrete		$\gamma_{inst}$	[-]	1,0	1,2								
waterfilled drill hole		$\gamma_{inst}$	[-]	1,4				no performance assessed					

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

**Injection system VMU plus for concrete**

**Performance**  
Characteristic values for rebar under tension loads

**Annex C9**

**Table C11: Characteristic values for rebar under shear load**

Rebar			Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 25	Ø 28	Ø 32	
<b>Steel failure without lever arm</b>												
Characteristic resistance	$V^0_{Rk,s}$	[kN]	$0,50 \cdot A_s \cdot f_{uk}^{1)}$									
Cross sectional area	$A_s$	[mm <sup>2</sup> ]	50	79	113	154	201	314	491	616	804	
Partial factor	$\gamma_{Ms,V}$	[-]	1,5 <sup>2)</sup>									
Ductility factor	$k_7$	[-]	1,0									
<b>Steel failure with lever arm</b>												
Characteristic bending moment	$M^0_{Rk,s}$	[Nm]	$1,2 \cdot W_{el} \cdot f_{uk}^{1)}$									
Elastic section modulus	$W_{el}$	[mm <sup>3</sup> ]	50	98	170	269	402	785	1534	2155	3217	
Partial factor	$\gamma_{Ms,V}$	[-]	1,5 <sup>2)</sup>									
<b>Concrete pry-out failure</b>												
Factor	$k_8$	[-]	2,0									
<b>Concrete edge failure</b>												
Effective length of anchor	$l_f$	[mm]	min( $h_{ef}$ ; 12 $d_{nom}$ )						min( $h_{ef}$ ; 300mm)			
Outside diameter of anchor	$d_{nom}$	[mm]	8	10	12	14	16	20	25	28	32	
Installation factor	$\gamma_{inst}$	[-]	1,0									

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

**Injection system VMU plus for concrete**

**Performance**  
Characteristic values for rebar under shear load

**Annex C10**

**Table C12:** Characteristic values for **rebar** under **seismic action, tension load**  
performance category **C1**

Rebar				Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 25	Ø 28	Ø 32	
<b>Steel failure</b>													
Characteristic resistance		$N_{Rk,s,C1}$	[kN]	$A_s \cdot f_{uk}^{1)}$									
Cross sectional area		$A_s$	[mm <sup>2</sup> ]	50	79	113	154	201	314	491	616	804	
Partial factor		$\gamma_{Ms,N}$	[-]	1,4 <sup>2)</sup>									
<b>Combined pull-out and concrete cone failure</b>													
<b>Characteristic bond resistance in concrete C20/25 to C50/60</b>													
Temperature range	I: 40°C/24°C	dry and wet concrete	$\tau_{Rk,C1}$	[N/mm <sup>2</sup> ]	2,5	3,1	3,7	3,7	3,7	3,7	3,8	4,5	4,5
	II: 80°C/50°C				1,6	2,2	2,7	2,7	2,7	2,7	2,8	3,1	3,1
	III: 120°C/72°C				1,3	1,6	2,0	2,0	2,0	2,0	2,1	2,4	2,4
	I: 40°C/24°C	waterfilled drill hole	$\tau_{Rk,C1}$	[N/mm <sup>2</sup> ]	2,5	2,5	3,7	3,7	3,7	no performance assessed			
	II: 80°C/50°C				1,6	1,9	2,7	2,7	2,7				
	III: 120°C/72°C				1,3	1,6	2,0	2,0	2,0				
<b>Installation factor</b>													
dry and wet concrete		$\gamma_{inst}$	[-]	1,0	1,2								
waterfilled drill hole		$\gamma_{inst}$	[-]	1,4					no performance assessed				

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

**Table C13:** Characteristic values for **rebar** under **seismic action, shear load**,  
performance category **C1**

Rebar				Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 25	Ø 28	Ø 32
<b>Steel failure <u>without</u> lever arm</b>												
Characteristic resistance		$V_{Rk,s,C1}$	[kN]	$0,35 \cdot A_s \cdot f_{uk}^{1)}$								
Cross sectional area		$A_s$	[mm <sup>2</sup> ]	50	79	113	154	201	314	491	616	804
Partial factor		$\gamma_{Ms,V}$	[-]	1,5 <sup>2)</sup>								
Ductility factor		$k_7$	[-]	1,0								

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

**Injection system VMU plus for concrete**

**Performance**

Characteristic values for **rebar** under **seismic action**, category **C1**

**Annex C11**

**Table C14: Displacement factor under tension loads<sup>1)</sup>**  
(threaded rod and internally threaded anchor rod)

Threaded rod			M8	M10 IG-M6	M12 IG-M8	M16 IG- M10	M20 IG-M12	M24 IG-M16	M27	M30 IG-M20
<b>Uncracked concrete C20/25, static and quasi-static action</b>										
Temperature range I: 40°C/24°C	$\delta_{N0}$ -factor	$\left[ \frac{\text{mm}}{\text{N/mm}^2} \right]$	0,021	0,023	0,026	0,031	0,036	0,041	0,045	0,049
	$\delta_{N\infty}$ -factor		0,030	0,033	0,037	0,045	0,052	0,060	0,065	0,071
Temperature range II: 80°C/50°C	$\delta_{N0}$ -factor		0,050	0,056	0,063	0,075	0,088	0,100	0,110	0,119
	$\delta_{N\infty}$ -factor		0,072	0,081	0,090	0,108	0,127	0,145	0,159	0,172
Temperature range III: 120°C/72°C	$\delta_{N0}$ -factor		0,050	0,056	0,063	0,075	0,088	0,100	0,110	0,119
	$\delta_{N\infty}$ -factor		0,072	0,081	0,090	0,108	0,127	0,145	0,159	0,172
<b>Cracked concrete C20/25, static and quasi-static action</b>										
Temperature range I: 40°C/24°C	$\delta_{N0}$ -factor	$\left[ \frac{\text{mm}}{\text{N/mm}^2} \right]$	0,090		0,070					
	$\delta_{N\infty}$ -factor		0,105		0,105					
Temperature range II: 80°C/50°C	$\delta_{N0}$ -factor		0,219		0,170					
	$\delta_{N\infty}$ -factor		0,255		0,245					
Temperature range III: 120°C/72°C	$\delta_{N0}$ -factor		0,219		0,170					
	$\delta_{N\infty}$ -factor		0,255		0,245					

<sup>1)</sup> Calculation of the displacement

$$\delta_{N0} = \delta_{N0}\text{-factor} \cdot \tau; \quad \tau: \text{acting bond stress for tension load}$$

$$\delta_{N\infty} = \delta_{N\infty}\text{-factor} \cdot \tau;$$

**Table C15: Displacement factor under shear load<sup>1)</sup>**  
(threaded rod and internally threaded anchor rod)

Threaded rod			M8	M10 IG-M6	M12 IG-M8	M16 IG- M10	M20 IG-M12	M24 IG-M16	M27	M30 IG-M20
<b>Uncracked concrete C20/25, static and quasi-static action</b>										
All temperature ranges	$\delta_{V0}$ -factor	$\left[ \frac{\text{mm}}{\text{N/mm}^2} \right]$	0,06	0,06	0,05	0,04	0,04	0,03	0,03	0,03
	$\delta_{V\infty}$ -factor		0,09	0,08	0,08	0,06	0,06	0,05	0,05	0,05
<b>Cracked concrete C20/25, static and quasi-static action</b>										
All temperature ranges	$\delta_{V0}$ -factor	$\left[ \frac{\text{mm}}{\text{N/mm}^2} \right]$	0,12	0,12	0,11	0,10	0,09	0,08	0,08	0,07
	$\delta_{V\infty}$ -factor		0,18	0,18	0,17	0,15	0,14	0,13	0,12	0,10

<sup>1)</sup> Calculation of the displacement

$$\delta_{V0} = \delta_{V0}\text{-factor} \cdot V; \quad V: \text{acting shear load}$$

$$\delta_{V\infty} = \delta_{V\infty}\text{-factor} \cdot V;$$

**Injection system VMU plus for concrete**

**Performance**  
Displacements (threaded rod and internally threaded anchor rod)

**Annex C12**



**Table C16: Displacement factor under tension load<sup>1)</sup> (rebar)**

Rebar		Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 25	Ø 28	Ø 32	
<b>Uncracked concrete C20/25, static and quasi-static action</b>											
Temperature range I: 40°C/24°C	δ <sub>N0</sub> -factor	mm [N/mm <sup>2</sup> ]	0,021	0,023	0,026	0,028	0,031	0,036	0,043	0,047	0,052
	δ <sub>N∞</sub> -factor		0,030	0,033	0,037	0,041	0,045	0,052	0,061	0,071	0,075
Temperature range II: 80°C/50°C	δ <sub>N0</sub> -factor		0,050	0,056	0,063	0,069	0,075	0,088	0,104	0,113	0,126
	δ <sub>N∞</sub> -factor		0,072	0,081	0,090	0,099	0,108	0,127	0,149	0,163	0,181
Temperature range III: 120°C/72°C	δ <sub>N0</sub> -factor		0,050	0,056	0,063	0,069	0,075	0,088	0,104	0,113	0,126
	δ <sub>N∞</sub> -factor		0,072	0,081	0,090	0,099	0,108	0,127	0,149	0,163	0,181
<b>Cracked concrete C20/25, static and quasi-static action</b>											
Temperature range I: 40°C/24°C	δ <sub>N0</sub> -factor	mm [N/mm <sup>2</sup> ]	0,090				0,070				
	δ <sub>N∞</sub> -factor		0,105				0,105				
Temperature range II: 80°C/50°C	δ <sub>N0</sub> -factor		0,219				0,170				
	δ <sub>N∞</sub> -factor		0,255				0,245				
Temperature range III: 120°C/72°C	δ <sub>N0</sub> -factor		0,219				0,170				
	δ <sub>N∞</sub> -factor		0,255				0,245				

<sup>1)</sup> Calculation of the displacement

$$\delta_{N0} = \delta_{N0\text{-factor}} \cdot \tau; \quad \tau: \text{acting bond stress for tension load}$$

$$\delta_{N\infty} = \delta_{N\infty\text{-factor}} \cdot \tau;$$

**Table C17: Displacement factor under shear load<sup>1)</sup> (rebar)**

Rebar		Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 25	Ø 28	Ø 32	
<b>Uncracked concrete C20/25, static and quasi-static action</b>											
All temperature ranges	δ <sub>V0</sub> -factor	mm [N/mm <sup>2</sup> ]	0,06	0,05	0,05	0,04	0,04	0,04	0,03	0,03	0,03
	δ <sub>V∞</sub> -factor		0,09	0,08	0,08	0,06	0,06	0,05	0,05	0,04	0,04
<b>Cracked concrete C20/25, static and quasi-static action</b>											
All temperature ranges	δ <sub>V0</sub> -factor	mm [N/mm <sup>2</sup> ]	0,12	0,12	0,11	0,11	0,10	0,09	0,08	0,07	0,06
	δ <sub>V∞</sub> -factor		0,18	0,18	0,17	0,16	0,15	0,14	0,12	0,11	0,10

<sup>1)</sup> Calculation of the displacement

$$\delta_{V0} = \delta_{V0\text{-factor}} \cdot V; \quad V: \text{acting shear load}$$

$$\delta_{V\infty} = \delta_{V\infty\text{-factor}} \cdot V;$$

**Injection system VMU plus for concrete**

**Performance**  
Displacements (rebar)

**Annex C13**