

Approval body for construction products  
and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and  
Laender Governments



## European Technical Assessment

**ETA-19/0483**  
**of 12 May 2021**

English translation prepared by DIBt - Original version in German language

### General Part

Technical Assessment Body issuing the  
European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

Injection system VME plus

Product family  
to which the construction product belongs

Bonded fastener for use in concrete

Manufacturer

MKT  
Metall-Kunststoff-Technik GmbH & Co. KG  
Auf dem Immel 2  
67685 Weilerbach  
DEUTSCHLAND

Manufacturing plant

Werk 1,D und Werk 2,D

This European Technical Assessment  
contains

39 pages including 3 annexes which form an integral part  
of this assessment

This European Technical Assessment is  
issued in accordance with Regulation (EU)  
No 305/2011, on the basis of

EAD 330499-01-0601, Edition 04/2020

This version replaces

ETA-19/0483 issued on 30 August 2019

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

**Specific Part**

**1 Technical description of the product**

The "Injection system VME Plus for concrete" is a bonded anchor consisting of a cartridge with injection mortar Injection mortar VME Plus and a steel element according to Annex A3 and A5. The steel element is placed into a drilled hole filled with injection mortar and is anchored via the bond between metal part, injection mortar and concrete. The product description is given in Annex A.

**2 Specification of the intended use in accordance with the applicable European Assessment Document**

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B. The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 and/or 100 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

**3 Performance of the product and references to the methods used for its assessment**

**3.1 Mechanical resistance and stability (BWR 1)**

Essential characteristic	Performance
Characteristic resistance to tension load (static and quasi-static loading)	See Annex B 3, C 1, C 3 to C 6, C 9 to 11, C 13 to C 15
Characteristic resistance to shear load (static and quasi-static loading)	See Annex C 2, C 7, C 12 and C 16
Displacements under short-term and long-term loading	See Annex C 18 to C 21
Characteristic resistance and displacements for seismic performance categories C1 and C2	See Annex C 8, C 17 to C 19

**3.2 Hygiene, health and the environment (BWR 3)**

Essential characteristic	Performance
Content, emission and/or release of dangerous substances	No performance assessed

English translation prepared by DIBt

**4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base**

In accordance with the European Assessment Document EAD 330499-01-0601 the applicable European legal act is: [96/582/EC].

The system to be applied is: 1

**5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document**

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.

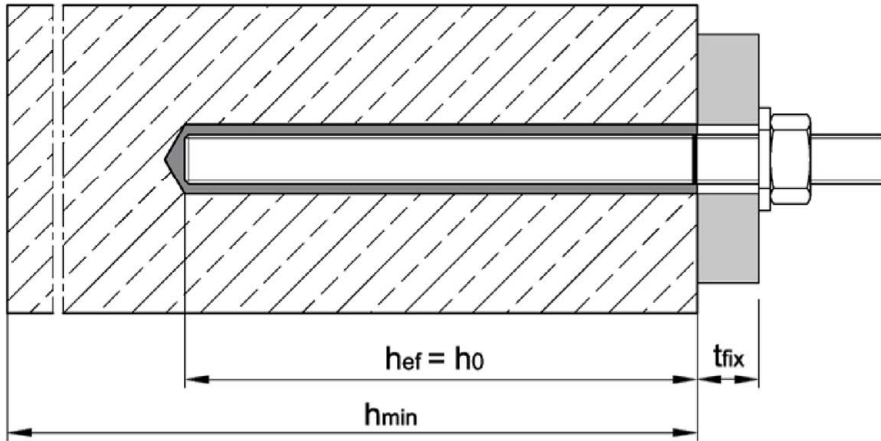
Issued in Berlin on 12 May 2021 by Deutsches Institut für Bautechnik

Dipl.-Ing. Beatrix Wittstock  
Head of Section


*beglaubigt:*  
Baderschneider

### Installation threaded rod M8 to M30


Pre-setting installation or through-setting installation (optional annular gap filled with mortar)



### Installation internally threaded anchor rod VMU-IG M6 to VMU-IG M20

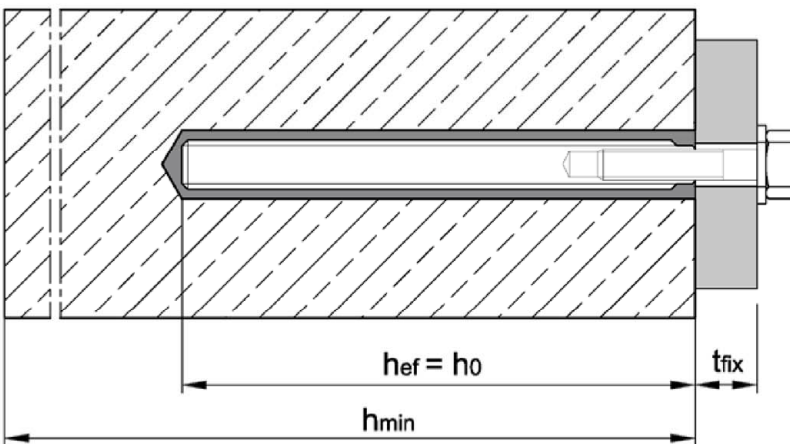

### Installation reinforcing bar $\varnothing 8$ to $\varnothing 32$

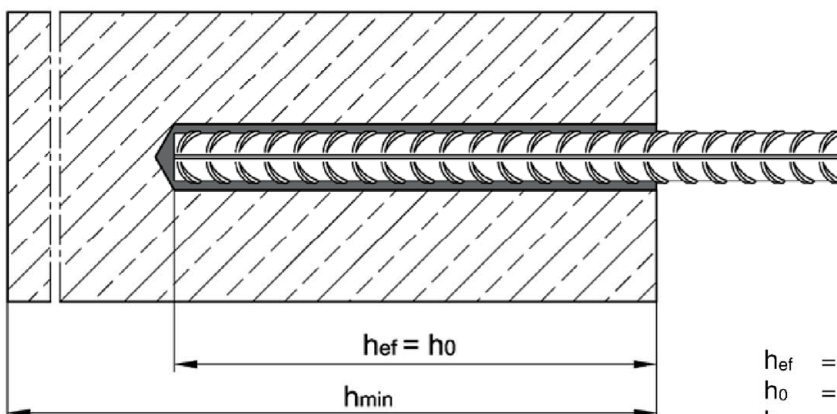

$h_{ef}$  = effective anchorage depth  
 $h_o$  = depth of drill hole  
 $h_{min}$  = minimum thickness of member  
 $t_{fix}$  = thickness of fixture

**Injection System VME plus** Keine Indexeinträge gefunden.


**Product description**  
Installation situation

**Annex A1**
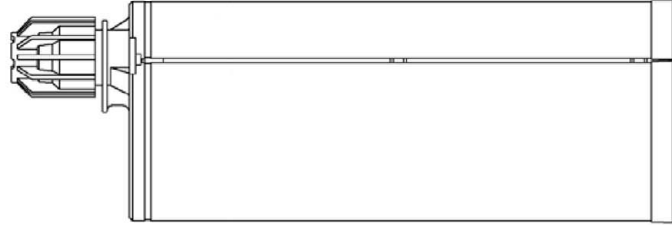
## Cartridge Injection Mortar VME plus

### Side-by-side cartridge


440 ml  
585 ml  
1400 ml




### Imprint:

VME plus,  
processing notes, batch number, shelf life, hazard-number, storage temperature, curing- and  
processing time, optional with travel scale

### Static Mixer



### Retaining washer and extension nozzle

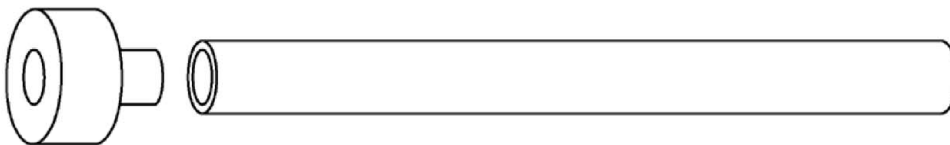

## Injection System VME plus

### Product description


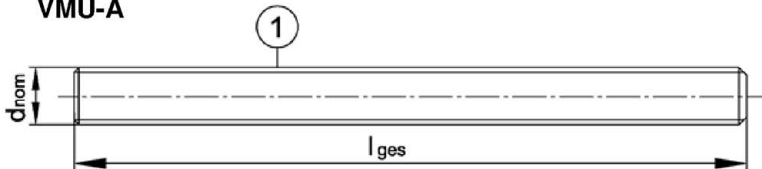
Cartridge, static mixer and retaining washer with extension nozzle

Annex A2

## Threaded rod

**Threaded rod VMU-A, V-A with washer and hexagon nut**  
**M8, M10, M12, M16, M20, M24, M27, M30** (zinc plated, A4, HCR)

**VMU-A**



Marking e.g.:  $\diamond$  M10

$\diamond$  identifying mark of manufacturing plant


M10 size of thread

additional marking:

A4 stainless steel

HC high corrosion resistant steel

**V-A**

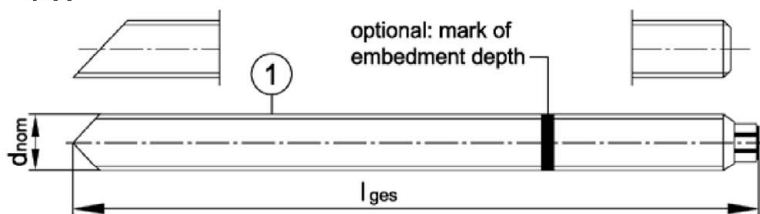

**Threaded rod VM-A** (material sold by the meter, to be cut at the required length)


**M8, M10, M12, M16, M20, M24, M27, M30** (zinc plated, A2, A4, HCR)

**Commercial standard threaded rod**

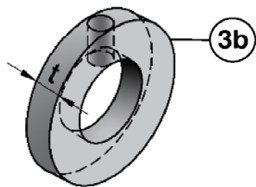
**M8, M10, M12, M16, M20, M24, M27, M30** (zinc plated, A2, A4, HCR) with:

- Materials, dimensions and mechanical properties see Table A1
- Inspection certificate 3.1 acc. to EN 10204:2004

## Washer with bore and reducing adapter for filling the gap between threaded rod and fixture




Thickness of washer with bore for diameter  
< M24:  $t = 5$  mm  
 $\geq$  M24:  $t = 6$  mm



## Internally threaded anchor rod

**VMU-IG M6, VMU-IG M8, VMU-IG M10, VMU-IG M12, VMU-IG M16, VMU-IG M20**

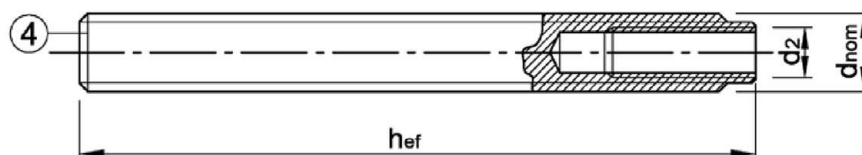(zinc plated, A4, HCR)



Marking e.g.:  $\diamond$  M8

$\diamond$  identifying mark of manufacturing plant

I internal thread

M8 size of internal thread

additional marking:

A4 stainless steel

HCR high corrosion resistant steel

## Injection System VME plus

### Product description

Threaded rod, internally threaded anchor rod and washer with bore

## Annex A3

**Table A1: Materials - Threaded rod and internally threaded anchor rod**

Part	Designation	Material						
<b>Steel, zinc plated</b> electroplated $\geq 5 \mu\text{m}$ acc. to EN ISO 4042:2018 or hot-dip galvanized $\geq 40 \mu\text{m}$ (50 $\mu\text{m}$ in average) acc. to EN ISO 1461:2009 and EN ISO 10684:2004+AC:2009 or sherardized $\geq 45 \mu\text{m}$ acc. to EN ISO 17668:2016								
1	Threaded rod	Property class	characteristic ultimate strength		characteristic yield strength		fracture elongation	EN ISO 683-4:2018, EN 10263:2001;  commercial standard threaded rod: EN ISO 898-1:2013
		4.6	$f_{uk}$ [N/mm <sup>2</sup> ]	400	$f_{yk}$ [N/mm <sup>2</sup> ]	240	$A_5 > 8 \%$	
		4.8		400		320	$A_5 > 8 \%$	
		5.6		500		300	$A_5 > 8 \%$	
		5.8		500		400	$A_5 > 8 \%$	
8.8	800	640		$A_5 \geq 12\% ^1)$				
2	Hexagon nut	4	for class 4.6 or 4.8 rods				EN ISO 898-2:2012	
		5	for class 4.6, 4.8, 5.6, 5.8 rods					
		8	for class 4.6, 4.8, 5.6, 5.8, 8.8 rods					
3a	Washer	e.g.: EN ISO 7089:2000, EN ISO 7093:2000, EN ISO 7094:2000, EN ISO 887:2006						
3b	Washer with bore	steel, zinc plated						
4	Internally threaded anchor rod	5.8	steel, electroplated or sherardized			$A_5 > 8\%$	EN ISO 683-4:2018	
		8.8				$A_5 > 8\%$		
<b>Stainless steel A2 <sup>2)</sup></b>		<b>CRC II</b> (Materials 1.4301 / 1.4307 / 1.4311 / 1.4567 / 1.4541)						
<b>Stainless steel A4</b>		<b>CRC III</b> (Materials 1.4401 / 1.4404 / 1.4571 / 1.4578 )						
<b>High corrosion resistant steel HCR</b>		<b>CRC V</b> (Materials 1.4529 / 1.4565)						
1	Threaded rod <sup>3)</sup>	Property class	characteristic ultimate strength		characteristic yield strength		fracture elongation	EN 10088-1:2014 EN ISO 3506-1:2020
		50	$f_{uk}$ [N/mm <sup>2</sup> ]	500	$f_{yk}$ [N/mm <sup>2</sup> ]	210	$A_5 > 8\%$	
		70		700		450	$A_5 \geq 12\% ^1)$	
80	800	600		$A_5 \geq 12\% ^1)$				
2	Hexagon nut <sup>3)</sup>	50	for class 50 rods				EN 10088-1:2014 EN ISO 3506-2:2020	
		70	for class 50 or 70 rods					
		80	for class 50, 70 or 80 rods					
3a	Washer	e.g.: EN ISO 7089:2000, EN ISO 7093:2000, EN ISO 7094:2000; EN ISO 887:2006						
3b	Washer with bore	stainless steel A4; high corrosion resistant steel HCR						
4	Internally threaded anchor rod	50	IG-M20			$A_5 > 8 \%$	EN 10088-1:2014	
		70	IG-M6 to IG-M16			$A_5 > 8 \%$		

<sup>1)</sup> fracture elongation  $A_5 > 8 \%$  for applications without requirements for seismic performance category C2

<sup>2)</sup> property classes 50 and 70

<sup>3)</sup> property classes 70 and 80 up to M24

**Injection System VME plus**

**Product description**

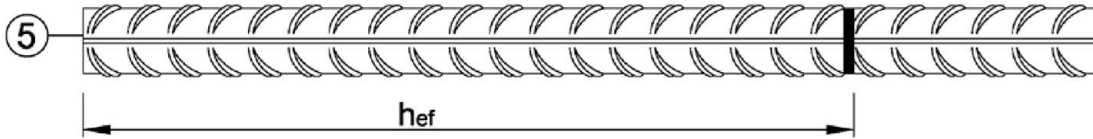
Materials - Threaded rod and internally threaded anchor rod

**Annex A4**



### Reinforcing bar

Ø 8, Ø 10, Ø 12, Ø 14, Ø 16, Ø 20, Ø 24, Ø 25, Ø 28, Ø 32



- Minimum value of related rip area  $f_{R,min}$  according to EN 1992-1-1:2004+AC:2010
- Rip height of the bar shall be in the range  $0,05d \leq h \leq 0,07d$   
(d: Nominal diameter of the bar; h: Rip height of the bar)

**Table A2: Material reinforcing bar**

Part	Designation	Material
<b>Rebar</b>		
5	Rebar EN 1992-1-1:2004+AC:2010, Annex C	Bars and de-coiled rods class B or C $f_{yk}$ and $k$ according to NDP or NCL acc. EN 1992-1-1/NA $f_{uk} = f_{tk} = k \cdot f_{yk}$

### Injection System VME plus

#### Product description

Product description and material reinforcing bar

**Annex A5**

Specification of intended use		
Static and quasi-static action	working life 50 years	working life 100 years
Threaded rod Internally threaded anchor rod Rebar	<b>M8 - M30</b> <b>VMU-IG M6 - VMU-IG M20</b> <b>Ø8 - Ø32</b>	
Base material	cracked or uncracked concrete	
	strength classes C20/25 to C50/60 compacted, reinforced or unreinforced normal weight concrete (without fibers) acc. to EN 206:2013+A1:2016	
Hole drilling	cracked concrete: hammer drilling / compressed air drilling / vaccum drilling	
	uncracked concrete: hammer drilling / compressed air drilling / vaccum drilling / diamond drilling	
Temperature range <sup>1)</sup>	I: -40°C to +40°C II: -40°C to +72°C	I: -40°C to +40°C II: -40°C to +72°C
Seismic action	performance category C1	performance category C2
Threaded rod Internally threaded anchor rod Rebar	<b>M8 - M30</b> <b>Ø8 - Ø32</b>	<b>M12 - M24</b> ---
Base material	cracked or uncracked concrete	
	strength classes C20/25 to C50/60 compacted, reinforced or unreinforced normal weight concrete (without fibers) acc. to EN 206:2013+A1:2016	
Hole drilling	hammer drilling / compressed air drilling / vaccum drilling	
Temperature range <sup>1)</sup>	I: -40°C to +40°C II: -40°C to +72°C	I: -40°C to +40°C II: -40°C to +72°C
<sup>1)</sup> Temperature Range I: max. long term temperature +24°C and max. short term temperature +40°C Temperature Range II: max. long term temperature +50°C and max. short term temperature +72°C		
<b>Injection System VME plus</b>		<b>Annex B1</b>
Intended use Specifications		

## Specification of intended use

### Use conditions (Environmental conditions):

- Structures subject to dry internal conditions: all materials
- For all other conditions:  
Intended use of Materials according to Annex A4, Table A1 corresponding corrosion resistance classes CRC according to EN 1993-1-4:2006+A1:2015

### Design:

- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the anchor is indicated on the design drawings (e.g. position of the anchor relative to reinforcement or to supports, etc.)
- Anchorages are designed under the responsibility of an engineer experienced in anchorages and concrete work
- Anchorages are designed in accordance with EN 1992-4:2018 or Technical Report TR 055, February 2018

### Installation:

- Dry or wet concrete or waterfilled drillholes (not seawater)
- Hole drilling by hammer drill, compressed air drill, vacuum drill or diamond drill mode
- Overhead installation allowed
- Anchor installation carried out by appropriately qualified personnel and under the responsibility of the person responsible for technical matters of the site
- Internally threaded anchor rod: Screws and threaded rods (incl. nut and washer) must at least correspond to the material and strength class of the internally threaded anchor rod used

## Injection System VME plus

Intended use  
Specifications

Annex B2

**Table B1: Installation parameters for threaded rods**

Threaded rod			M8	M10	M12	M16	M20	M24	M27	M30
Diameter of threaded rod	$d=d_{nom}$	[mm]	8	10	12	16	20	24	27	30
Nominal drill hole diameter	$d_0$	[mm]	10	12	14	18	22	28	30	35
Effective anchorage depth	$h_{ef,min}$	[mm]	60	60	70	80	90	96	108	120
	$h_{ef,max}$	[mm]	160	200	240	320	400	480	540	600
Diameter of clearance hole in the fixture	Pre-setting installation $d_f \leq$	[mm]	9	12	14	18	22	26	30	33
	Through setting installation $d_f \leq$	[mm]	12	14	16	20	24	30	33	40
Maximum installation torque	$max.T_{inst} \leq$	[Nm]	10	20	40 (35) <sup>1)</sup>	60	100	170	250	300
Minimum thickness of member	$h_{min}$	[mm]	$h_{ef} + 30mm \geq 100mm$			$h_{ef} + 2d_0$				
Minimum spacing	$s_{min}$	[mm]	40	50	60	75	95	115	125	140
Minimum edge distance	$c_{min}$	[mm]	35	40	45	50	60	65	75	80

<sup>1)</sup> max. installation torque for property class 4.6

**Table B2: Installation parameters for internally threaded anchor rods**

Internally threaded anchor rod			IG-M 6	IG-M 8	IG-M 10	IG-M 12	IG-M 16	IG-M 20
Inner diameter of threaded rod	$d_2$	[mm]	6	8	10	12	16	20
Outer diameter of threaded rod <sup>1)</sup>	$d=d_{nom}$	[mm]	10	12	16	20	24	30
Nominal drill hole diameter	$d_0$	[mm]	12	14	18	22	28	35
Effective anchorage depth	$h_{ef,min}$	[mm]	60	70	80	90	96	120
	$h_{ef,max}$	[mm]	200	240	320	400	480	600
Diameter of clearance hole in the fixture	$d_f \leq$	[mm]	7	9	12	14	18	22
Maximum installation torque	$max.T_{inst} \leq$	[Nm]	10	10	20	40	60	100
Minimum screw-in depth	$l_{IG}$	[mm]	8	8	10	12	16	20
Minimum thickness of member	$h_{min}$	[mm]	$h_{ef} + 30mm \geq 100mm$			$h_{ef} + 2d_0$		
Minimum spacing	$s_{min}$	[mm]	50	60	75	95	115	140
Minimum edge distance	$c_{min}$	[mm]	40	45	50	60	65	80

<sup>1)</sup> with metric thread acc. to EN 1993-1-8:2005+AC:2009

**Table B3: Installation parameters for rebar**

Rebar			Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 24	Ø 25	Ø 28	Ø 32	
Diameter of rebar	$d=d_{nom}$	[mm]	8	10	12	14	16	20	24	25	28	32	
Nominal drill hole diameter <sup>1)</sup>	$d_0$	[mm]	10	12	14	16	18	20	25	30	32	35	40
			12	14	16	18	20	25	30	32	35	40	
Effective anchorage depth	$h_{ef,min}$	[mm]	60	60	70	75	80	90	96	100	112	128	
	$h_{ef,max}$	[mm]	160	200	240	280	320	400	480	500	560	640	
Minimum thickness of member	$h_{min}$	[mm]	$h_{ef} + 30 mm \geq 100 mm$				$h_{ef} + 2d_0$						
Minimum spacing	$s_{min}$	[mm]	40	50	60	70	75	95	120	120	130	150	
Minimum edge distance	$c_{min}$	[mm]	35	40	45	50	50	60	70	70	75	85	






<sup>1)</sup> for Ø8, Ø10, Ø12, Ø24 and Ø25 both nominal drill hole diameter can be used

**Injection System VME plus**


Intended use  
Installation parameters

**Annex B3**

**Table B4: Parameter for cleaning and setting tools**

Threaded rod	Internally threaded anchor rod	Rebar	Drill bit Ø	Brush Ø	min. Brush Ø
					
[-]	[-]	Ø [mm]	d <sub>0</sub> [mm]	d <sub>b</sub> [mm]	d <sub>b,min</sub> [mm]
M8		8	10	11,5	10,5
M10	VMU-IG M6	8 / 10	12	13,5	12,5
M12	VMU-IG M8	10 / 12	14	15,5	14,5
		12	16	17,5	16,5
M16	VMU-IG M10	14	18	20,0	18,5
		16	20	22,0	20,5
M20	VMU-IG M12		22	24,0	22,5
		20	25	27,0	25,5
M24	VMU-IG M16		28	30,0	28,5
M27		24 / 25	30	31,8	30,5
		24 / 25	32	34,0	32,5
M30	VMU-IG M20	28	35	37,0	35,5
		32	40	43,5	40,5

**Table B5: Retaining washer**

Drill bit Ø		Installation direction and use		
d <sub>0</sub> [mm]	[-]	↓	→	↑
10	No retaining washer required			
12				
14				
16				
18	VM-IA 18	h <sub>ef</sub> > 250mm	h <sub>ef</sub> > 250mm	all
20	VM-IA 20			
22	VM-IA 22			
25	VM-IA 25			
28	VM-IA 28			
30	VM-IA 30			
32	VM-IA 32			
35	VM-IA 35			
40	VM-IA 40			



**Vacuum drill bit**

Vacuum drill bit (MKT Hollow drill bit SB, Würth Hammer drill bit with suction or Heller Duster Expert hollow drill bit system) and a vacuum cleaner with minimum negative pressure of 253 hPa and flow rate of minimum 42 l/s (150 m³/h)



**Recommended compressed air tool (min 6 bar)**  
Drill bit diameter (d<sub>0</sub>): all diameters

**Injection System VME plus**

**Intended use**  
Cleaning and setting tools

**Annex B4**

**Table B6: Working time and curing time**

Concrete temperature	Working time	Minimum curing time	
		dry concrete	wet concrete
0°C to +4°C	90 min	144 h	288 h
+5°C to +9°C	80 min	48 h	96 h
+10°C to +14°C	60 min	28 h	56 h
+15°C to +19°C	40 min	18 h	36 h
+20°C to +24°C	30 min	12 h	24 h
+25°C to +34°C	12 min	9 h	18 h
+35°C to +39°C	8 min	6 h	12 h
+40°C	8 min	4 h	8 h
<b>Cartridge temperature</b>	+5°C to +40°C		

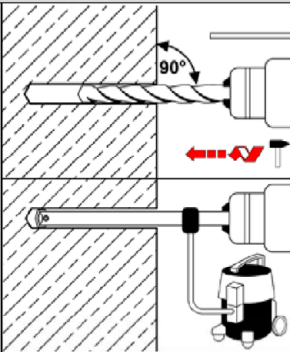
**Injection System VME plus**

**Intended use**  
Working and curing time

**Annex B5**




## Installation instructions

### Drilling of the drill hole and cleaning: Hammer drilling, compressed air drilling and vacuum drilling

<b>1</b>		<p><b>Hammer drilling or compressed air drilling:</b> Drill with hammer drill or compressed air drill a hole into the base material with prescribed nominal drill hole diameter (Table B1, B2 or B3) and selected drillhole depth. Continue with <u>step 2</u>. In case of aborted drill hole, the drill hole shall be filled with mortar.</p> <p><b>Vacuum drilling:</b> see Annex B4 Drill drillhole with prescribed nominal drill hole diameter (Table B1, B2 or B3) and selected drillhole depth. This drilling method removes dust and cleans the drillhole during drilling. Continue with step 3. In case of aborted drill hole, the drill hole shall be filled with mortar.</p>
----------	---	--

**Attention! Standing water in the drill hole must be removed before cleaning!**

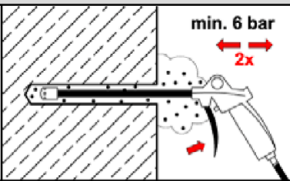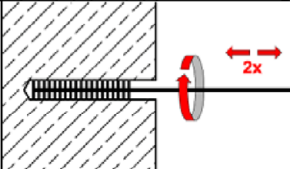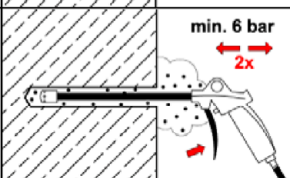**Cleaning:** dry, wet and water-filled drill holes with all diameter in uncracked and cracked concrete (Cleaning not applicable when using vacuum drilling)

<b>2a</b>		<p>Starting from the bottom or back of the drill hole, blow out the hole with compressed air (min. 6 bar) a minimum of <b>two</b> times until return air stream is free of noticeable dust. If the drillhole ground is not reached, an extension must be used.</p>
<b>2b</b>		<p>Check brush diameter (Table B4). Brush the hole with an appropriate sized wire brush <math>\geq d_{b,min}</math> (Table B4) a minimum of <b>two</b> times. If the drillhole ground is not reached with the brush, an appropriate brush extension must be used.</p>
<b>2c</b>		<p>Starting from the bottom or back of the drill hole, blow out the hole with compressed air (min. 6 bar) again a minimum of <b>two</b> times until return air stream is free of noticeable dust. If the drillhole ground is not reached, an extension must be used.</p>

**After cleaning, the drillhole has to be protected against re-contamination in an appropriate way, until dispensing the mortar in the drillhole. If necessary, the cleaning has to be repeated directly before dispensing the mortar. In-flowing water must not contaminate the drillhole again.**

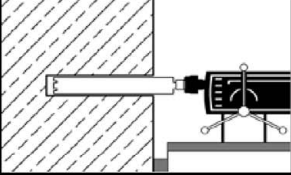
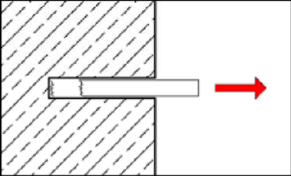
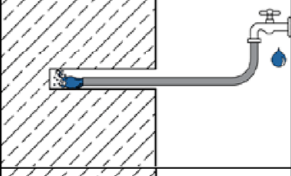
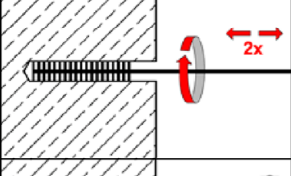
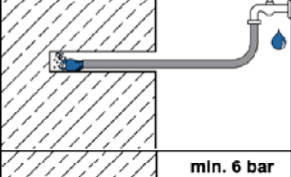
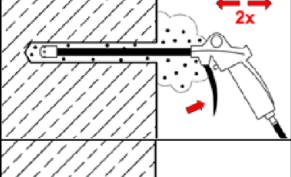
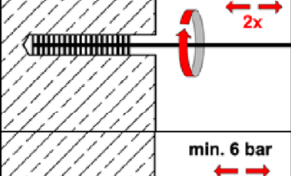
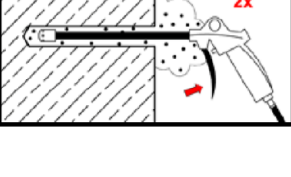
### Injection System VME plus

#### Intended use

Installation instructions – Drilling and cleaning: Hammer drilling, compressed air drilling and vacuum drilling

### Annex B6

## Installation instructions (continuation)

Drilling of the drill hole and cleaning: Diamond drilling		
1		Drill a hole into the base material with prescribed nominal drill hole diameter (Table B1, B2 or B3) and selected drillhole depth. Continue with step 2. In case of aborted drill hole, the drill hole shall be filled with mortar.
<b>Cleaning:</b> dry, wet and water-filled drill holes with all diameter in uncracked concrete		
2a		Remove drill core at least up to the nominal drill hole depth and check drill hole depth.
2b		Flush drill hole with water, starting from the bottom until clear water gets out of the drill hole.
2c		Check brush diameter (Table B4). Brush the hole with an appropriate sized wire brush $\geq d_{b,min}$ (Table B4) a minimum of <b>two</b> times. If the drillhole ground is not reached with the brush, an appropriate brush extension must be used.
2d		Flush drill hole again with water, starting from the bottom until clear water gets out of the drill hole.
2e		Starting from the bottom or back of the drill hole, blow out the hole with compressed air (min. 6 bar) again a minimum of <b>two</b> times until return air stream is free of noticeable dust. If the drillhole ground is not reached, an extension must be used.
2f		Check brush diameter (Table B4). Brush the hole again with an appropriate sized wire brush $\geq d_{b,min}$ (Table B4) a minimum of <b>two</b> times. If the drillhole ground is not reached with the brush, an appropriate brush extension must be used.
2g		Starting from the bottom or back of the drill hole, blow out the hole with compressed air (min. 6 bar) again a minimum of <b>two</b> times until return air stream is free of noticeable dust. If the drillhole ground is not reached, an extension must be used.






### Injection System VME plus

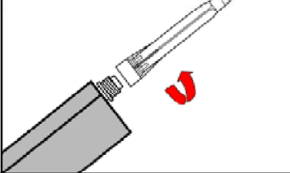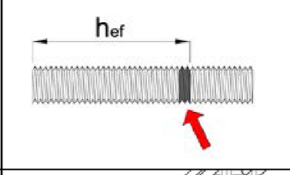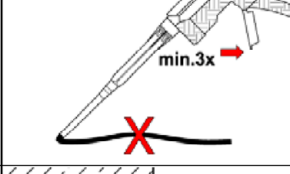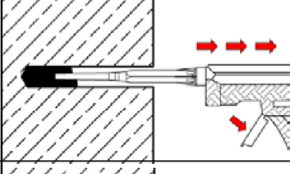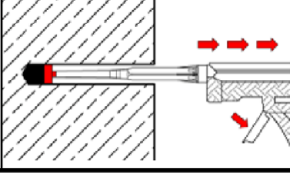**Intended use**  
Installation instructions – Drilling and cleaning: Diamond drilling

**Annex B7**



### Installation instructions (continuation)







Injection		
3		Attach the supplied static-mixing nozzle to the cartridge and load the cartridge into the correct dispensing tool. For every working interruption longer than the recommended working time (Table B6) as well as for new cartridges, a new static-mixer shall be used.
4		Prior to inserting the rod into the filled drillhole, the position of the embedment depth shall be marked on the threaded rod or rebar.
5		Prior to dispensing into the drill hole, squeeze out separately a minimum of three full strokes and discard non-uniformly mixed adhesive components until the mortar shows a consistent grey or red colour.
6		Starting from the bottom or back of the cleaned drill hole fill the hole up to approximately two-thirds with adhesive. Slowly withdraw the static mixing nozzle as the hole fills to avoid air pockets. If the drill hole ground is not reached, an appropriate extension nozzle shall be used. Observe temperature dependent working times given in Table B6.
7		Retaining washer and mixer nozzle extensions shall be used according to Table B5 for the following applications: <ul style="list-style-type: none"> <li>• Horizontal installation (horizontal direction) and ground installation (vertical downwards direction): Drill bit-<math>\varnothing</math> <math>d_0 \geq 18</math> mm and anchorage depth <math>h_{ef} &gt; 250</math>mm</li> <li>• Overhead installation: Drill bit-<math>\varnothing</math> <math>d_0 \geq 18</math> mm</li> </ul>

#### Injection System VME plus

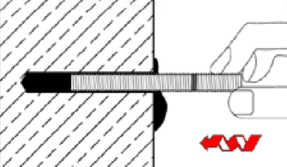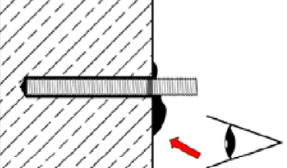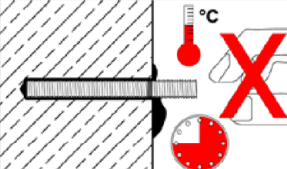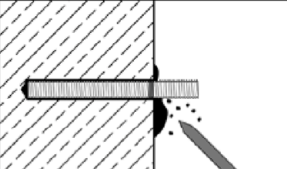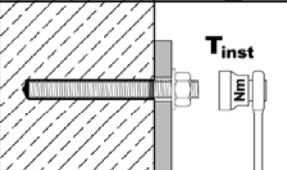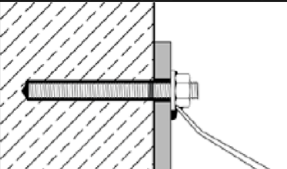Intended use  
Installation instructions – Injection

Annex B8

## Installation instructions (continuation)

Setting the fastening element		
8		Push the threaded rod or reinforcing bar into the hole while turning slightly to ensure proper distribution of the adhesive until the embedment depth is reached. The anchor shall be free of dirt, grease, oil or other foreign material.
9		Make sure that excess mortar is visible at the top of the hole and in case of through-setting installation also in the fixture. If these requirements are not maintained, repeat application before end of working time! For overhead installation, the anchor should be fixed (e.g. by wedges).
10		Allow the adhesive to cure to the specified time prior to applying any load or torque. Do not move or load the anchor until it is fully cured (attend Table B6).
11		Remove excess mortar.
12		The fixture can be mounted after curing time. Apply installation torque $T_{inst}$ according to Table B1 or B2.
13		In case of pre-setting installation the annular gap between anchor rod and fixture can optionally be filled with mortar. Therefore, replace regular washer by washer with drill and plug on reducing adapter on static mixer. Annular gap is completely filled, when excess mortar seeps out.

### Injection System VME plus

#### Intended use

Installation instructions – Setting the fastening element

Annex B9

**Table C1: Characteristic steel resistance for threaded rods under tension load**

Threaded rod				M8	M10	M12	M16	M20	M24	M27	M30
<b>Steel failure</b>											
Cross sectional area $A_s$ [mm <sup>2</sup> ]				36,6	58,0	84,3	157	245	353	459	561
<b>Characteristic resistance under tension load <sup>1)</sup></b>											
Steel, zinc plated	Property class 4.6 and 4.8	$N_{Rk,s}$	[kN]	15 (13)	23 (21)	34	63	98	141	184	224
	Property class 5.6 and 5.8	$N_{Rk,s}$	[kN]	18 (17)	29 (27)	42	78	122	176	230	280
	Property class 8.8	$N_{Rk,s}$	[kN]	29 (27)	46 (43)	67	125	196	282	368	449
Stainless steel	A2, A4 and HCR Property class 50	$N_{Rk,s}$	[kN]	18	29	42	79	123	177	230	281
	A2, A4 and HCR Property class 70	$N_{Rk,s}$	[kN]	26	41	59	110	171	247	_ <sup>3)</sup>	_ <sup>3)</sup>
	A4 and HCR Property class 80	$N_{Rk,s}$	[kN]	29	46	67	126	196	282	_ <sup>3)</sup>	_ <sup>3)</sup>
<b>Partial factors <sup>2)</sup></b>											
Steel, zinc plated	Property class 4.6	$\gamma_{Ms,N}$	[-]	2,0							
	Property class 4.8	$\gamma_{Ms,N}$	[-]	1,5							
	Property class 5.6	$\gamma_{Ms,N}$	[-]	2,0							
	Property class 5.8	$\gamma_{Ms,N}$	[-]	1,5							
	Property class 8.8	$\gamma_{Ms,N}$	[-]	1,5							
Stainless steel	A2, A4 and HCR Property class 50	$\gamma_{Ms,N}$	[-]	2,86							
	A2, A4 and HCR Property class 70	$\gamma_{Ms,N}$	[-]	1,87						_ <sup>3)</sup>	_ <sup>3)</sup>
	A4 and HCR Property class 80	$\gamma_{Ms,N}$	[-]	1,6						_ <sup>3)</sup>	_ <sup>3)</sup>

<sup>1)</sup> the characteristic resistances apply for all anchor rods with the cross sectional area  $A_s$  specified here: VMU-A, V-A, VM-A. For commercial standard threaded rods with a smaller cross sectional area (e.g. hot-dip galvanized threaded rods M8, M10 according to EN ISO 10684:2004 + AC:2009), the values in brackets are valid.

<sup>2)</sup> in absence of national regulation

<sup>3)</sup> Anchor type not part of the ETA

**Injection System VME plus**

**Performance**

Characteristic steel resistance for **threaded rods** under **tension load**

**Annex C1**

**Table C2: Characteristic steel resistance for threaded rods under shear load**

Threaded rod			M8	M10	M12	M16	M20	M24	M27	M30
<b>Steel failure</b>										
Cross sectional area $A_s$ [mm <sup>2</sup> ]			36,6	58,0	84,3	157	245	353	459	561
<b>Characteristic resistance under shear load <sup>1)</sup></b>										
<b>Steel failure <u>without</u> lever arm</b>										
Steel, zinc plated	Property class 4.6 and 4.8	$V_{Rk,s}^0$ [kN]	9 (8)	14 (13)	20	38	59	85	110	135
	Property class 5.6 and 5.8	$V_{Rk,s}^0$ [kN]	11 (10)	17 (16)	25	47	74	106	138	168
	Property class 8.8	$V_{Rk,s}^0$ [kN]	15 (13)	23 (21)	34	63	98	141	184	224
Stainless steel	A2, A4 and HCR, property class 50	$V_{Rk,s}^0$ [kN]	9	15	21	39	61	88	115	140
	A2, A4 and HCR, property class 70	$V_{Rk,s}^0$ [kN]	13	20	30	55	86	124	-	-
	A4 and HCR, property class 80	$V_{Rk,s}^0$ [kN]	15	23	34	63	98	141	-	-
<b>Steel failure <u>with</u> lever arm</b>										
Steel, zinc plated	Property class 4.6 and 4.8	$M_{Rk,s}^0$ [Nm]	15 (13)	30 (27)	52	133	260	449	666	900
	Property class 5.6 and 5.8	$M_{Rk,s}^0$ [Nm]	19 (16)	37 (33)	65	166	324	560	833	1123
	Property class 8.8	$M_{Rk,s}^0$ [Nm]	30 (26)	60 (53)	105	266	519	896	1333	1797
Stainless steel	A2, A4 and HCR, property class 50	$M_{Rk,s}^0$ [Nm]	19	37	66	167	325	561	832	1125
	A2, A4 and HCR, property class 70	$M_{Rk,s}^0$ [Nm]	26	52	92	232	454	784	_ <sup>3)</sup>	_ <sup>3)</sup>
	A4 and HCR, property class 80	$M_{Rk,s}^0$ [Nm]	30	59	105	266	519	896	_ <sup>3)</sup>	_ <sup>3)</sup>
<b>Partial factor <sup>2)</sup></b>										
Steel, zinc plated	Property class 4.6	$\gamma_{Ms,V}$ [-]				1,67				
	Property class 4.8	$\gamma_{Ms,V}$ [-]				1,25				
	Property class 5.6	$\gamma_{Ms,V}$ [-]				1,67				
	Property class 5.8	$\gamma_{Ms,V}$ [-]				1,25				
	Property class 8.8	$\gamma_{Ms,V}$ [-]				1,25				
Stainless steel	A2, A4 and HCR, property class 50	$\gamma_{Ms,V}$ [-]				2,38				
	A2, A4 and HCR, property class 70	$\gamma_{Ms,V}$ [-]				1,56		_ <sup>3)</sup>		_ <sup>3)</sup>
	A4 and HCR, property class 80	$\gamma_{Ms,V}$ [-]				1,33		_ <sup>3)</sup>		_ <sup>3)</sup>

<sup>1)</sup> the characteristic resistances apply for all anchor rods with the cross sectional area  $A_s$  specified here: VMU-A, V-A, VM-A. For commercial standard threaded rods with a smaller cross sectional area (e.g. hot-dip galvanized threaded rods M8, M10 according to EN ISO 10684:2004 + AC:2009), the values in brackets are valid.

<sup>2)</sup> in absence of national regulation

<sup>3)</sup> Anchor type not part of the ETA

<b>Injection System VME plus</b>	<b>Annex C2</b>
<b>Performance</b> Characteristic <b>steel resistance</b> for <b>threaded rods</b> under <b>shear load</b>	

**Table C3:** Characteristic values for **concrete cone** and **splitting failure**

Threaded rods / Internally threaded anchor rods / Rebars			all sizes
<b>Concrete cone failure</b>			
Factor $k_1$	uncracked concrete	$k_{ucr,N}$ [-]	11,0
	cracked concrete	$k_{cr,N}$ [-]	7,7
Edge distance		$c_{cr,N}$ [mm]	$1,5 \cdot h_{ef}$
Spacing		$s_{cr,N}$ [mm]	$2 \cdot c_{cr,N}$
<b>Splitting failure</b>			
Characteristic resistance		$N_{Rk,sp}^0$ [kN]	$\min ( N_{Rk,p} ; N_{Rk,c}^0 )$
Edge distance	$h/h_{ef} \geq 2,0$	$c_{cr,sp}$ [mm]	$1,0 \cdot h_{ef}$
	$2,0 > h/h_{ef} > 1,3$		$2 \cdot h_{ef} (2,5 - h / h_{ef})$
	$h/h_{ef} \leq 1,3$		$2,4 \cdot h_{ef}$
Spacing		$s_{cr,sp}$ [mm]	$2 \cdot c_{cr,sp}$

**Injection System VME plus**

**Performance**  
Characteristic values for **concrete cone** and **splitting failure**

**Annex C3**

**Table C4: Characteristic values of tension load for threaded rods, static and quasi-static action, working life 50 years**

Threaded rod				M8	M10	M12	M16	M20	M24	M27	M30
<b>Steel failure</b>											
Characteristic resistance		$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}$ (or see Table C1)							
Partial factor		$\gamma_{Ms,N}$	[-]	see Table C1							
<b>Combined pull-out and concrete failure</b>											
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>											
Temperature range I: 40°C / 24°C	hammer- or compressed air drilling	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	20	20	19	19	18	17	16	16
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	15	15	15	14	13	13	12	12
Temperature range I: 40°C / 24°C	vacuum drilling	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	17 (16) <sup>1)</sup>	16	16	16 (15) <sup>1)</sup>	15	14	14	13
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	14	14	14	13	13	12	12	11
<b>Characteristic bond resistance in <u>cracked</u> concrete C20/25</b>											
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	7,0	7,0	8,5	8,5	8,5	8,5	8,5	8,5
Temperature range II: 72°C / 50°C		$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	6,0	6,0	7,0	7,0	7,0	7,0	7,0	7,0
<b>Reductionfactor <math>\psi^0_{sus}</math> in concrete C20/25</b>											
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\psi^0_{sus}$	[-]	0,80							
Temperature range II: 72°C / 50°C		$\psi^0_{sus}$	[-]	0,68							
Increasing factors for concrete	C25/30	$\psi_c$	[-]	1,02							
	C30/37		[-]	1,04							
	C35/45		[-]	1,07							
	C40/50		[-]	1,08							
	C45/55		[-]	1,09							
	C50/60		[-]	1,10							
<b>Concrete cone failure</b>											
Relevant parameter				see Table C3							
<b>Splitting failure</b>											
Relevant parameter				see Table C3							
<b>Installation factor</b>											
dry or wet concrete		$\gamma_{inst}$	[-]	1,0							
waterfilled drill hole		$\gamma_{inst}$	[-]	1,2							

<sup>1)</sup> value in brackets: characteristic bond resistance for waterfilled drill holes

**Injection System VME plus**

**Performance**  
Characteristic values of **tension loads** for **threaded rods**, working life 50 years

**Annex C4**

**Table C5: Characteristic values of tension load for threaded rods, static and quasi-static action, working life 100 years**

Threaded rod				M8	M10	M12	M16	M20	M24	M27	M30
<b>Steel failure</b>											
Characteristic resistance		$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}$ (or see Table C1)							
Partial factor		$\gamma_{Ms,N}$	[-]	see Table C1							
<b>Combined pull-out and concrete failure</b>											
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>											
Temperature range I: 40°C / 24°C	Hammer- or compressed air drilling	$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	20	20	19	19	18	17	16	16
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	15	15	15	14	13	13	12	12
Temperature range I: 40°C / 24°C	Vacuum drilling	$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	17 (16) <sup>1)</sup>	16	16	16 (15) <sup>1)</sup>	15	14	14	13
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	14	14	14	13	13	12	12	11
<b>Characteristic bond resistance in <u>cracked</u> concrete C20/25</b>											
Temperature range I: 40°C / 24°C	Hammer-, compressed air or vacuum drilling	$\tau_{Rk,cr,100}$	[N/mm <sup>2</sup> ]	6,5	6,5	7,5	7,5	7,5	7,5	7,5	7,5
Temperature range II: 72°C / 50°C		$\tau_{Rk,cr,100}$	[N/mm <sup>2</sup> ]	5,5	5,5	6,5	6,5	6,5	6,5	6,5	6,5
Increasing factors for concrete	C25/30	$\psi_c$	[-]	1,02							
	C30/37		[-]	1,04							
	C35/45		[-]	1,07							
	C40/50		[-]	1,08							
	C45/55		[-]	1,09							
	C50/60		[-]	1,10							
<b>Concrete cone failure</b>											
Relevant parameter				see Table C3							
<b>Splitting failure</b>											
Relevant parameter				see Table C3							
<b>Installation factor</b>											
dry or wet concrete		$\gamma_{inst}$	[-]	1,0							
waterfilled drill hole		$\gamma_{inst}$	[-]	1,2							

<sup>1)</sup> Value in brackets: characteristic bond resistance for waterfilled drill holes

**Injection System VME plus**

**Performance**  
Characteristic values of **tension loads** for **threaded rods**, working life 100 years

**Annex C5**

**Table C6: Characteristic values of tension load for threaded rods, static and quasi-static action, working life 50 and 100 years, diamond drilling in uncracked concrete**

Threaded rod				M8	M10	M12	M16	M20	M24	M27	M30
<b>Steel failure</b>											
Characteristic resistance		$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}$ (or see Table C1)							
Partial factor		$\gamma_{Ms,N}$	[-]	see Table C1							
<b>Combined pull-out and concrete failure</b>											
<b>Characteristic bond resistance in uncracked concrete C20/25</b> Working life 50 years											
Temperature range I: 40°C / 24°C	diamond drilling	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	15	14	14	13	12	12	11	11
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	12	12	11	10	9,5	9,5	9,0	9,0
<b>Reduction factor <math>\psi^0_{sus}</math> in uncracked concrete C20/25</b>											
Temperature range I: 40°C / 24°C	diamond drilling	$\psi^0_{sus}$	[-]	0,77							
Temperature range II: 72°C / 50°C		$\psi^0_{sus}$	[-]	0,72							
<b>Characteristic bond resistance in uncracked concrete C20/25</b> Working life 100 years											
Temperature range I: 40°C / 24°C	diamond drilling	$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	15	14	14	13	12	12	11	11
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	11	11	10	10	9,5	9,0	8,5	8,5
Increasing factors for concrete	C25/30	$\psi_c$	[-]	1,04							
	C30/37		[-]	1,08							
	C35/45		[-]	1,12							
	C40/50		[-]	1,15							
	C45/55		[-]	1,17							
	C50/60		[-]	1,19							
<b>Concrete cone failure</b>											
Relevant parameter				see Table C3							
<b>Splitting failure</b>											
Relevant parameter				see Table C3							
<b>Installation factor</b>											
dry or wet concrete		$\gamma_{inst}$	[-]	1,0							
waterfilled drill hole		$\gamma_{inst}$	[-]	1,2				1,4			

**Injection System VME plus**

**Performance**  
Characteristic values of tension loads for threaded rods,  
working life 50 and 100 years, diamond drilling

**Annex C6**



**Table C7: Characteristic values of shear loads for threaded rods, static and quasi-static action**

Threaded rod		M8	M10	M12	M16	M20	M24	M27	M30	
<b>Steel failure <u>without</u> lever arm</b>										
Characteristic shear resistance Steel, property class 4.6, 4.8, 5.6 and 5.8	$V_{Rk,s}^0$	[kN]	0,6 · A <sub>s</sub> · f <sub>uk</sub> or see Table C2							
Characteristic shear resistance Steel, property class 8.8 Stainless steel A2, A4 and HCR (all property classes)	$V_{Rk,s}^0$	[kN]	0,5 · A <sub>s</sub> · f <sub>uk</sub> or see Table C2							
Ductility factor	k <sub>7</sub>	[-]	1,0							
Partial factor	γ <sub>Ms,V</sub>	[-]	see Table C2							
<b>Steel failure <u>with</u> lever arm</b>										
Characteristic bending resistance	$M_{Rk,s}^0$	[Nm]	1,2 · W <sub>el</sub> · f <sub>uk</sub> or see Table C2							
Elastic section modulus	W <sub>el</sub>	[mm <sup>3</sup> ]	31	62	109	277	541	935	1387	1874
Partial factor	γ <sub>Ms,V</sub>	[-]	see Table C2							
<b>Concrete pry-out failure</b>										
Pry-out factor	k <sub>8</sub>	[-]	2,0							
<b>Concrete edge failure</b>										
Effective length of anchor	l <sub>f</sub>	[mm]	min (h <sub>ef</sub> ; 12 d <sub>nom</sub> )						min (h <sub>ef</sub> ; 300mm)	
Outside diameter of anchor	d <sub>nom</sub>	[mm]	8	10	12	16	20	24	27	30
Installation factor	γ <sub>inst</sub>	[-]	1,0							

**Injection System VME plus**

**Performance**  
Characteristic values of **shear loads** for **threaded rods**

**Annex C7**

**Table C8: Characteristic values of tension load for threaded rods, seismic action (performance category C1 + C2), working life 50 and 100 years**

Threaded rod			M8	M10	M12	M16	M20	M24	M27	M30
<b>Tension loads</b>										
<b>Steel failure</b>										
Characteristic resistance <b>C1</b>	$N_{Rk,s,C1}$	[kN]	$1,0 \cdot N_{Rk,s}$							
Characteristic resistance <b>C2</b> steel, zinc plated, property class 8.8 stainless steel A4 and HCR, property class $\geq 70$	$N_{Rk,s,C2}$	[kN]	- <sup>1)</sup>	$1,0 \cdot N_{Rk,s}$						- <sup>1)</sup>
Partial factor	$\gamma_{Ms,N}$	[-]	see Table C1							
<b>Combined pull-out and concrete failure</b>										
<b>Characteristic bond resistance in concrete C20/25 to C50/60</b>										
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\tau_{Rk,C1}$ [N/mm <sup>2</sup> ]	7,0	7,0	8,5	8,5	8,5	8,5	8,5	8,5
		$\tau_{Rk,C2}$ [N/mm <sup>2</sup> ]	- <sup>1)</sup>		5,8	4,8	5,0	5,1	- <sup>1)</sup>	
Temperature range II: 72°C / 50°C		$\tau_{Rk,C1}$ [N/mm <sup>2</sup> ]	6,0	6,0	7,0	7,0	7,0	7,0	7,0	7,0
		$\tau_{Rk,C2}$ [N/mm <sup>2</sup> ]	- <sup>1)</sup>		5,0	4,1	4,3	4,4	- <sup>1)</sup>	
<b>Installation factor</b>										
Dry or wet concrete	$\gamma_{inst}$	[-]	1,0							
Waterfilled drill hole	$\gamma_{inst}$	[-]	1,2							

<sup>1)</sup> No performance assessed

**Table C9: Characteristic values of shear loads for threaded rods, seismic action (performance category C1 + C2)**

Threaded rod			M8	M10	M12	M16	M20	M24	M27	M30
<b>Shear loads</b>										
<b>Steel failure <u>without</u> lever arm</b>										
Characteristic resistance <b>C1</b>	$V_{Rk,s,C1}$	[kN]	$0,7 \cdot V^0_{Rk,s}$							
Characteristic resistance <b>C2</b> steel, zinc plated, property class 8.8 stainless steel A4 and HCR, property class $\geq 70$	$V_{Rk,s,C2}$	[kN]	- <sup>1)</sup>	$0,7 \cdot V^0_{Rk,s}$						- <sup>1)</sup>
Partial factor	$\gamma_{Ms,N}$	[-]	see Table C2							
Factor for anchorages	without annular gap	$\alpha_{gap}$	[-]	1,0						
	with annular gap between threaded rod and fixture			0,5						

<sup>1)</sup> No performance assessed

**Injection System VME plus**

**Performance**  
Characteristic values for **threaded rods** under **seismic action**

**Annex C8**

**Table C10: Characteristic values of tension loads for internally threaded anchor rod, static and quasi-static action, working life 50 years**

Internally threaded anchor rod				VMU-IG M 6	VMU-IG M 8	VMU-IG M 10	VMU-IG M 12	VMU-IG M 16	VMU-IG M 20
<b>Steel failure <sup>1)</sup></b>									
Characteristic resistance, steel, zinc plated, property class	5.8	$N_{Rk,s}$	[kN]	10	17	29	42	76	123
	8.8	$N_{Rk,s}$	[kN]	16	27	46	67	121	196
Partial factor 5.8 and 8.8		$\gamma_{Ms,N}$	[-]	1,5					
Characteristic resistance, Stainless steel A4 / HCR, property class 70		$N_{Rk,s}$	[kN]	14	26	41	59	110	124 <sup>2)</sup>
	Partial factor		$\gamma_{Ms,N}$	[-]	1,87				
<b>Combined pull-out and concrete failure</b>									
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>									
Temperature range I: 40°C / 24°C	hammer- or compressed air drilling	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	20	19	19	18	17	16
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	15	15	14	13	13	12
Temperature range I: 40°C / 24°C	vacuum drilling	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	16	16	16 (15) <sup>3)</sup>	15	14	13
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	14	14	13	13	12	11
<b>Characteristic bond resistance in <u>cracked</u> concrete C20/25</b>									
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	7,0	8,5	8,5	8,5	8,5	8,5
Temperature range II: 72°C / 50°C		$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	6,0	7,0	7,0	7,0	7,0	7,0
<b>Reductionfactor <math>\psi_{sus}^0</math></b>									
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\psi_{sus}^0$	[-]	0,80					
Temperature range II: 72°C / 50°C		$\psi_{sus}^0$	[-]	0,68					
Increasing factor for concrete		$\psi_c$	C25/30	1,02					
			C30/37	1,04					
			C35/45	1,07					
			C40/50	1,08					
			C45/55	1,09					
			C50/60	1,10					
<b>Concrete cone failure</b>									
Relevant parameter				see Table C3					
<b>Splitting failure</b>									
Relevant parameter				see Table C3					
<b>Installation factor</b>									
dry or wet concrete		$\gamma_{inst}$	[-]	1,0					
waterfilled drill hole		$\gamma_{inst}$	[-]	1,2					

<sup>1)</sup> Fastening screws or threaded rods (incl. nut and washer) must comply with the appropriate material and property class of the internally threaded anchor rod. The characteristic tension resistance for steel failure of the given strength class are valid for the internally threaded anchor rod and the fastening element.

<sup>2)</sup> for VMU-IG M20: property class 50

<sup>3)</sup> value in bracket is valid for waterfilled drill hole

**Injection System VME plus**

**Performance**

Characteristic values of tension loads for internally threaded anchor rod, working life 50 years

**Annex C9**

**Table C11: Characteristic values of tension loads for internally threaded anchor rod static and quasi-static action, working life 100 years**

Internally threaded anchor rod				VMU-IG M 6	VMU-IG M 8	VMU-IG M 10	VMU-IG M 12	VMU-IG M 16	VMU-IG M 20
<b>Steel failure <sup>1)</sup></b>									
Characteristic resistance, steel, zinc plated, property class	5.8	$N_{Rk,s}$	[kN]	10	17	29	42	76	123
	8.8	$N_{Rk,s}$	[kN]	16	27	46	67	121	196
Partial factor 5.8 and 8.8		$\gamma_{Ms,N}$	[-]	1,5					
Characteristic resistance, Stainless steel A4 / HCR, property class 70		$N_{Rk,s}$	[kN]	14	26	41	59	110	124 <sup>2)</sup>
	Partial factor		$\gamma_{Ms,N}$	[-]	1,87				
<b>Combined pull-out and concrete failure</b>									
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>									
Temperature range I: 40°C / 24°C	hammer- or compressed air drilling	$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	20	19	19	18	17	16
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	15	15	14	13	13	12
Temperature range I: 40°C / 24°C	vacuum drilling	$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	16	16	16 (15) <sup>3)</sup>	15	14	13
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	14	14	13	13	12	11
<b>Characteristic bond resistance in <u>cracked</u> concrete C20/25</b>									
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\tau_{Rk,cr,100}$	[N/mm <sup>2</sup> ]	6,5	7,5	7,5	7,5	7,5	7,5
Temperature range II: 72°C / 50°C		$\tau_{Rk,cr,100}$	[N/mm <sup>2</sup> ]	5,5	6,5	6,5	6,5	6,5	6,5
Increasing factor for concrete	$\psi_c$	C25/30		1,02					
		C30/37		1,04					
		C35/45		1,07					
		C40/50		1,08					
		C45/55		1,09					
		C50/60		1,10					
<b>Concrete cone failure</b>									
Relevant parameter				see Table C3					
<b>Splitting failure</b>									
Relevant parameter				see Table C3					
<b>Installation factor</b>									
dry or wet concrete		$\gamma_{inst}$	[-]	1,0					
waterfilled drill hole		$\gamma_{inst}$	[-]	1,2					

<sup>1)</sup> fastening screws or threaded rods (incl. nut and washer) must comply with the appropriate material and property class of the internally threaded anchor rod. The characteristic tension resistance for steel failure of the given strength class are valid for the internally threaded anchor rod and the fastening element.

<sup>2)</sup> for VMU-IG M20: property class 50

<sup>3)</sup> value in bracket is valid for waterfilled drill hole

**Injection System VME plus**

**Performance**

Characteristic values of tension loads for internally threaded anchor rod, working life 100 years

**Annex C10**

**Table C12: Characteristic values of tension loads for internally threaded anchor rod, static and quasi-static action, working life 50 and 100 years, diamond drilling**

Internally threaded anchor rod				VMU-IG M 6	VMU-IG M 8	VMU-IG M 10	VMU-IG M 12	VMU-IG M 16	VMU-IG M 20
<b>Steel failure <sup>1)</sup></b>									
Characteristic resistance, steel, zinc plated, property class	5.8	$N_{Rk,s}$	[kN]	10	17	29	42	76	123
	8.8	$N_{Rk,s}$	[kN]	16	27	46	67	121	196
Partial factor 5.8 and 8.8		$\gamma_{Ms,N}$	[-]	1,5					
Characteristic resistance, stainless steel A4 / HCR, property class 70		$N_{Rk,s}$	[kN]	14	26	41	59	110	124 <sup>2)</sup>
Partial factor		$\gamma_{Ms,N}$	[-]	1,87					
<b>Combined pull-out and concrete failure</b>									
<b>Characteristic bond resistance in uncracked concrete C20/25</b>								<b>Working life 50 years</b>	
Temperature range I: 40°C / 24°C	diamond drilling	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	14	14	13	12	12	11
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	12	11	10	9,5	9,5	9,0
<b>Reduktionsfaktor <math>\psi^{0}_{sus}</math></b>									
Temperature range I: 40°C / 24°C	diamond drilling	$\psi^{0}_{sus}$	[-]	0,77					
Temperature range II: 72°C / 50°C		$\psi^{0}_{sus}$	[-]	0,72					
<b>Characteristic bond resistance in uncracked concrete C20/25</b>								<b>Working life 100 years</b>	
Temperature range I: 40°C / 24°C	diamond drilling	$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	14	14	13	12	12	11
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	11	10	10	9,5	9,0	8,5
Increasing factor for $\tau_{Rk,ucr}$		$\psi_c$	C25/30	1,04					
			C30/37	1,08					
			C35/45	1,12					
			C40/50	1,15					
			C45/55	1,17					
			C50/60	1,19					
<b>Concrete cone failure</b>									
Relevant parameter				see Table C3					
<b>Splitting failure</b>									
Relevant parameter				see Table C3					
<b>Installation factor</b>									
dry or wet concrete		$\gamma_{inst}$	[-]	1,0					
waterfilled drill hole		$\gamma_{inst}$	[-]	1,2		1,4			

<sup>1)</sup> fastening screws or threaded rods (incl. nut and washer) must comply with the appropriate material and property class of the internally threaded anchor rod. The characteristic tension resistance for steel failure of the given strength class are valid for the internally threaded anchor rod and the fastening element.

<sup>2)</sup> for VMU-IG M20: property class 50

<sup>3)</sup> value in bracket is valid for waterfilled drill hole

### Injection System VME plus

#### Performance

Characteristic values of tension loads for internally threaded anchor rod, working life 50 and 100 years, diamond drilling

**Annex C11**

**Table C13: Characteristic values of shear loads for internally threaded anchor rod, static and quasi-static action**

Internally threaded anchor rod				VMU-IG M 6	VMU-IG M 8	VMU-IG M 10	VMU-IG M 12	VMU-IG M 16	VMU-IG M 20	
<b>Steel failure <u>without</u> lever arm <sup>1)</sup></b>										
Steel, zinc plated	Characteristic resistance, property class	5.8	$V_{Rk,s}^0$ [kN]	6	10	17	25	45	74	
		8.8	$V_{Rk,s}^0$ [kN]	8	14	23	34	60	98	
	Partial factor 5.8 and 8.8		$\gamma_{Ms,v}$	[-]	1,25					
Stainless steel	Characteristic resistance, A4 / HCR, property class 70		$V_{Rk,s}^0$ [kN]	7	13	20	30	55	62 <sup>2)</sup>	
	Partial factor		$\gamma_{Ms,v}$	[-]	1,56					2,38
Ductility factor			$k_7$	[-]	1,0					
<b>Steel failure <u>with</u> lever arm <sup>1)</sup></b>										
Steel, zinc plated	Characteristic bending resistance, property class	5.8	$M_{Rk,s}^0$ [Nm]	8	19	37	66	167	325	
		8.8	$M_{Rk,s}^0$ [Nm]	12	30	60	105	267	519	
	Partial factor 5.8 and 8.8		$\gamma_{Ms,v}$	[-]	1,25					
Stainless steel	Characteristic bending resistance A4 / HCR, property class 70		$M_{Rk,s}^0$ [Nm]	11	26	53	92	234	643 <sup>2)</sup>	
	Partial factor		$\gamma_{Ms,v}$	[-]	1,56					2,38
<b>Concrete pry-out failure</b>										
Pry-out factor			$k_8$	[-]	2,0					
<b>Concrete edge failure</b>										
Effective length of anchor			$l_f$ [mm]	min ( $h_{ef}; 12 d_{nom}$ )					min ( $h_{ef}; 300mm$ )	
Outside diameter of anchor			$d_{nom}$ [mm]	10	12	16	20	24	30	
Installation factor			$\gamma_{inst}$	[-]	1,0					

<sup>1)</sup> fastening screws or threaded rods (incl. nut and washer) must comply with the appropriate material and property class of the internally threaded anchor rod (exception: VMU-IG M20). The characteristic shear resistance for steel failure of the given strength class are valid for the internally threaded anchor rod and the fastening element.

<sup>2)</sup> for VMU-IG M20: Internally threaded rod: property class 50;  
Fastening screws or threaded rods (incl. nut and washer): property class 70

**Injection System VME plus**

**Performance**  
Characteristic values of **shear loads** for **internally threaded anchor rod**

**Annex C12**

**Table C14: Characteristic values of tension loads for rebar, static and quasi-static action, working life 50 years**

Reinforcing bar			Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 24	Ø 25	Ø 28	Ø 32	
<b>Steel failure</b>													
Characteristic tension resistance	$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}^{1)}$										
Cross sectional area	$A_s$	[mm <sup>2</sup> ]	50	79	113	154	201	314	452	491	616	804	
Partial factor	$\gamma_{Ms,N}$	[-]	1,4 <sup>2)</sup>										
<b>Combined pull-out and concrete failure</b>													
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>													
Temperature range I: 40°C / 24°C	hammer- and compressed air drilling	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	16	16	16	16	16	16	15	15	15	15
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	12	12	12	12	12	12	12	12	11	11
Temperature range I: 40°C / 24°C	vacuum drilling	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	14 (13) <sup>3)</sup>	14 (13) <sup>3)</sup>	13	13	13	13	13	13	13	13
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	12 (11) <sup>3)</sup>	12 (11) <sup>3)</sup>	12 (11) <sup>3)</sup>	11	11	11	11	11	11	11
<b>Characteristic bond resistance in <u>cracked</u> concrete C20/25</b>													
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	7,0	7,0	8,5	8,5	8,5	8,5	8,5	8,5	8,5	8,5
Temperature range II: 72°C / 50°C		$\tau_{Rk,cr}$	[N/mm <sup>2</sup> ]	6,0	6,0	7,0	7,0	7,0	7,0	7,0	7,0	7,0	7,0
<b>Reductionfactor <math>\psi_{sus}^0</math></b>													
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\psi_{sus}^0$	[-]	0,80									
Temperature range II: 72°C / 50°C		$\psi_{sus}^0$	[-]	0,68									
Increasing factor for concrete	$\psi_c$	C25/30		1,02									
		C30/37		1,04									
		C35/45		1,07									
		C40/50		1,08									
		C45/55		1,09									
		C50/60		1,10									
<b>Concrete cone failure</b>													
Relevant parameter	see Table C3												
<b>Splitting failure</b>													
Relevant parameter	see Table C3												
<b>Installation factor</b>													
dry or wet concrete	$\gamma_{inst}$	[-]	1,0										
waterfilled drill hole	$\gamma_{inst}$	[-]	1,2										

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

<sup>3)</sup> value in brackets: characteristic bond resistance for waterfilled drill holes

**Injection System VME plus**

**Performance**

Characteristic values of **tension loads** for rebar, working life 50 years

**Annex C13**

**Table C15: Characteristic values of tension loads for rebar, static and quasi-static action, working life 100 years**

Reinforcing bar			Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 24	Ø 25	Ø 28	Ø 32	
<b>Steel failure</b>													
Characteristic tension resistance	$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}^{1)}$										
Cross sectional area	$A_s$	[mm <sup>2</sup> ]	50	79	113	154	201	314	452	491	616	804	
Partial factor	$\gamma_{Ms,N}$	[-]	1,4 <sup>2)</sup>										
<b>Combined pull-out and concrete failure</b>													
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>													
Temperature range I: 40°C / 24°C	hammer- and compressed air drilling	$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	16	16	16	16	16	16	15	15	15	15
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	12	12	12	12	12	12	12	12	11	11
Temperature range I: 40°C / 24°C	vacuum drilling	$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	14 (13) <sup>3)</sup>	14 (13) <sup>3)</sup>	13	13	13	13	13	13	13	13
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	12 (11) <sup>3)</sup>	12 (11) <sup>3)</sup>	12 (11) <sup>3)</sup>	11	11	11	11	11	11	11
<b>Characteristic bond resistance in <u>cracked</u> concrete C20/25</b>													
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\tau_{Rk,cr,100}$	[N/mm <sup>2</sup> ]	6,5	6,5	7,5	7,5	7,5	7,5	7,5	7,5	7,5	7,5
Temperature range II: 72°C / 50°C		$\tau_{Rk,cr,100}$	[N/mm <sup>2</sup> ]	5,5	5,5	6,5	6,5	6,5	6,5	6,5	6,5	6,5	6,5
Increasing factor for concrete	$\psi_c$	C25/30		1,02									
		C30/37		1,04									
		C35/45		1,07									
		C40/50		1,08									
		C45/55		1,09									
		C50/60		1,10									
<b>Concrete cone failure</b>													
Relevant parameter	see Table C3												
<b>Splitting failure</b>													
Relevant parameter	see Table C3												
<b>Installation factor</b>													
dry or wet concrete	$\gamma_{inst}$	[-]	1,0										
waterfilled drill hole	$\gamma_{inst}$	[-]	1,2										

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

<sup>3)</sup> value in brackets: characteristic bond resistance for waterfilled drill holes

**Injection System VME plus**

**Performance**

Characteristic values of **tension loads** for rebar, working life 100 years

**Annex C14**



**Table C16:** Characteristic values of **tension loads** for rebar,  
**static and quasi-static action**, working life **50 and 100 years**,  
**diamond drilling**

Reinforcing bar			Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 24	Ø 25	Ø 28	Ø 32	
<b>Steel failure</b>													
Characteristic tension resistance	$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}^{1)}$										
Cross sectional area	$A_s$	[mm <sup>2</sup> ]	50	79	113	154	201	314	452	491	616	804	
Partial factor	$\gamma_{Ms,N}$	[-]	1,4 <sup>2)</sup>										
<b>Combined pull-out and concrete failure</b>													
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>													
<b>Working life 50 years</b>													
Temperature range I: 40°C / 24°C	diamond drilling	$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	14	13	13	13	12	12	11	11	11	11
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr}$	[N/mm <sup>2</sup> ]	11	11	10	10	10	9,5	9,5	9,5	9,0	9,0
<b>Reductionfactor <math>\psi_{sus}^0</math></b>													
Temperature range I: 40°C / 24°C	diamond drilling	$\psi_{sus}^0$	[-]	0,77									
Temperature range II: 72°C / 50°C		$\psi_{sus}^0$	[-]	0,72									
<b>Characteristic bond resistance in <u>uncracked</u> concrete C20/25</b>													
<b>Working life 100 years</b>													
Temperature range I: 40°C / 24°C	diamond drilling	$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	14	13	13	13	12	12	11	11	11	11
Temperature range II: 72°C / 50°C		$\tau_{Rk,ucr,100}$	[N/mm <sup>2</sup> ]	11	10	10	10	9,5	9,0	9,0	9,0	8,5	8,5
Increasing factor for concrete		$\psi_c$	C25/30	1,04									
			C30/37	1,08									
			C35/45	1,12									
			C40/50	1,15									
			C45/55	1,17									
			C50/60	1,19									
<b>Concrete cone failure</b>													
Relevant parameter			see Table C3										
<b>Splitting failure</b>													
Relevant parameter			see Table C3										
<b>Installation factor</b>													
dry or wet concrete	$\gamma_{inst}$	[-]	1,0										
waterfilled drill hole	$\gamma_{inst}$	[-]	1,2					1,4					

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

**Injection System VME plus**

**Performance**

Characteristic values of **tension loads** for rebar,  
working life **50 and 100 years**, **diamond drilling**

**Annex C15**

**Table C17: Characteristic values of shear loads for rebar, static and quasi-static action**

Reinforcing bar		Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 24	Ø 25	Ø 28	Ø 32	
<b>Steel failure <u>without</u> lever arm</b>												
Characteristic shear resistance	$V^0_{Rk,s}$ [kN]	$0,50 \cdot A_s \cdot f_{uk}^{1)}$										
Cross sectional area	$A_s$ [mm <sup>2</sup> ]	50	79	113	154	201	314	452	491	616	804	
Partial factor	$\gamma_{Ms,V}$ [-]	1,5 <sup>2)</sup>										
Ductility factor	$k_7$ [-]	1,0										
<b>Steel failure <u>with</u> lever arm</b>												
Characteristic bending resistance	$M^0_{Rk,s}$ [Nm]	$1,2 \cdot W_{el} \cdot f_{uk}^{1)}$										
Elastic section modulus	$W_{el}$ [mm <sup>3</sup> ]	50	98	170	269	402	785	1357	1534	2155	3217	
Partial factor	$\gamma_{Ms,V}$ [-]	1,5 <sup>2)</sup>										
<b>Concrete pry-out failure</b>												
Pry-out factor	$k_8$ [-]	2,0										
<b>Concrete edge failure</b>												
Effective length of rebar	$l_r$ [mm]	min ( $h_{ef}$ ; 12 $d_{nom}$ )							min ( $h_{ef}$ ; 300mm)			
Outside diameter of rebar	$d_{nom}$ [mm]	8	10	12	14	16	20	24	25	28	32	
Installation factor	$\gamma_{inst}$ [-]	1,0										

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

**Injection System VME plus**

**Performance**  
Characteristic values of **shear loads** for rebar

**Annex C16**

**Table C18:** Characteristic values of **tension load** for rebar,  
**seismic action** (performance category **C1**), working life **50 and 100 years**

Reinforcing bar		Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 24	Ø 25	Ø 28	Ø 32	
<b>Steel failure</b>												
Characteristic resistance	$N_{Rk,s,C1}$	[kN]	$A_s \cdot f_{uk}^{1)}$									
Cross sectional area	$A_s$	[mm <sup>2</sup> ]	50	79	113	154	201	314	452	491	616	804
Partial factor	$\gamma_{Ms,N}$	[-]	1,4 <sup>2)</sup>									
<b>Combined pull-out and concrete failure</b>												
<b>Characteristic bond resistance in concrete C20/25 to C50/60</b>												
Temperature range I: 40°C / 24°C	hammer-, compressed air or vacuum drilling	$\tau_{Rk,C1}$	[N/mm <sup>2</sup> ]	7,0	7,0	8,5	8,5	8,5	8,5	8,5	8,5	8,5
Temperature range II: 72°C / 50°C		$\tau_{Rk,C1}$	[N/mm <sup>2</sup> ]	6,0	6,0	7,0	7,0	7,0	7,0	7,0	7,0	7,0
<b>Installation factor</b>												
dry or wet concrete	$\gamma_{inst}$	[-]	1,0									
waterfilled drill hole	$\gamma_{inst}$	[-]	1,2									

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

**Table C19:** Characteristic values of **shear loads** for rebar,  
**seismic action** (performance category **C1**)

Reinforcing bar		Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 24	Ø 25	Ø 28	Ø 32	
<b>Steel failure <u>without</u> lever arm</b>												
Characteristic resistance	$V_{Rk,s,C1}$	[kN]	$0,35 \cdot A_s \cdot f_{uk}^{1)}$									
Cross sectional area	$A_s$	[mm <sup>2</sup> ]	50	79	113	154	201	314	452	491	616	804
Partial factor	$\gamma_{Ms,V}$	[-]	1,5 <sup>2)</sup>									
Ductility factor	$k_7$	[-]	1,0									

<sup>1)</sup>  $f_{uk}$  shall be taken from the specifications of reinforcing bars

<sup>2)</sup> in absence of national regulation

**Injection System VME plus**

**Performance**  
Characteristic values for rebar under seismic action

**Annex C17**

**Table C20: Displacements under tension load, threaded rod**

Threaded rod	M8	M10	M12	M16	M20	M24	M27	M30		
<b>Hammer-, compressed air or vacuum drilling</b>										
<b>Displacement factor<sup>1)</sup></b>										
<b>Uncracked concrete, static and quasi-static action, working life 50 and 100 years</b>										
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	mm [ $\frac{mm}{N/mm^2}$ ]	0,028	0,029	0,030	0,033	0,035	0,038	0,039	0,041
	$\delta_{N\infty}$ - factor		0,028	0,029	0,030	0,033	0,035	0,038	0,039	0,041
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,038	0,039	0,040	0,044	0,047	0,051	0,052	0,055
	$\delta_{N\infty}$ - factor		0,047	0,049	0,051	0,055	0,059	0,064	0,067	0,070
<b>Displacement factor<sup>1)</sup></b>										
<b>Cracked concrete, static and quasi-static action, working life 50 and 100 years</b>										
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	mm [ $\frac{mm}{N/mm^2}$ ]	0,069	0,071	0,072	0,074	0,076	0,079	0,081	0,082
	$\delta_{N\infty}$ - factor		0,100	0,115	0,122	0,128	0,135	0,142	0,155	0,171
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,092	0,095	0,096	0,099	0,102	0,106	0,109	0,110
	$\delta_{N\infty}$ - factor		0,134	0,154	0,163	0,172	0,181	0,189	0,207	0,229
<b>Displacement</b>										
<b>Uncracked and cracked concrete, seismic action (C2)</b>										
All temperature ranges	$\delta_{N,C2}$ (DLS)	[mm]	_2)	0,21	0,24	0,27	0,36	_2)		
	$\delta_{N,C2}$ (ULS)			0,54	0,51	0,54	0,63			
<b>Diamond drilling</b>										
<b>Displacement factor<sup>1)</sup></b>										
<b>Uncracked concrete, static and quasi-static action, working life 50 years</b>										
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	mm [ $\frac{mm}{N/mm^2}$ ]	0,011	0,012	0,012	0,013	0,014	0,014	0,015	0,015
	$\delta_{N\infty}$ - factor		0,018	0,019	0,019	0,020	0,022	0,023	0,024	0,025
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,013	0,014	0,014	0,015	0,016	0,016	0,018	0,018
	$\delta_{N\infty}$ - factor		0,052	0,053	0,055	0,058	0,062	0,065	0,068	0,070
<b>Displacement factor<sup>1)</sup></b>										
<b>Uncracked concrete, static and quasi-static action, working life 100 years</b>										
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	mm [ $\frac{mm}{N/mm^2}$ ]	0,011	0,012	0,012	0,013	0,014	0,014	0,015	0,015
	$\delta_{N\infty}$ - factor		0,020	0,021	0,021	0,023	0,024	0,025	0,026	0,027
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,013	0,014	0,014	0,015	0,016	0,016	0,018	0,018
	$\delta_{N\infty}$ - factor		0,038	0,039	0,040	0,043	0,045	0,047	0,049	0,051

<sup>1)</sup> Calculation of the displacement

$$\delta_{N0} = \delta_{N0}\text{-factor} \cdot \tau; \quad \tau: \text{acting bond stress under tension load}$$

$$\delta_{N\infty} = \delta_{N\infty}\text{-factor} \cdot \tau;$$

<sup>2)</sup> No Performance assessed

**Injection System VME plus**

**Performance**  
Displacements (threaded rod under tension load)

**Annex C18**

**Table C21: Displacements** under **shear load**, threaded rod

Threaded rod		M8	M10	M12	M16	M20	M24	M27	M30	
<b>All drilling methods</b>										
<b>Displacement factor<sup>1)</sup></b>										
<b>Uncracked and cracked concrete, static and quasi-static action</b>										
All temperature ranges	$\delta_{v0}$ - factor	[mm/(kN)]	0,06	0,06	0,05	0,04	0,04	0,03	0,03	0,03
	$\delta_{v\infty}$ - factor		0,09	0,08	0,08	0,06	0,06	0,05	0,05	0,05
<b>Displacement</b>										
<b>Uncracked and cracked concrete, seismic action (C2)</b>										
All temperature ranges	$\delta_{V,C2}$ (DLS)	[mm]	_2)	3,1	3,4	3,5	4,2	_2)		
	$\delta_{V,C2}$ (ULS)			6,0	7,6	7,3	10,9			

<sup>1)</sup> Calculation of the displacement

$$\delta_{v0} = \delta_{v0}\text{- factor} \cdot V; \quad V: \text{acting shear load}$$

$$\delta_{v\infty} = \delta_{v\infty}\text{- factor} \cdot V;$$

<sup>2)</sup> No Performance assessed

**Injection System VME plus**

**Performance**

Displacements (threaded rod under shear load)

**Annex C19**

**Table C22: Displacement factors<sup>1)</sup> under tension load, internally threaded anchor rod**

Internally threaded anchor rod		VMU-IG M 6	VMU-IG M 8	VMU-IG M 10	VMU-IG M 12	VMU-IG M 16	VMU-IG M 20	
<b>Hammer-, compressed air or vaccum drilling</b>								
<b>Uncracked concrete, static and quasi-static action, working life 50 and 100 years</b>								
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	[mm [N/mm <sup>2</sup> ]]	0,029	0,030	0,033	0,035	0,038	0,041
	$\delta_{N\infty}$ - factor		0,029	0,030	0,033	0,035	0,038	0,041
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,039	0,040	0,044	0,047	0,051	0,055
	$\delta_{N\infty}$ - factor		0,049	0,051	0,055	0,059	0,064	0,070
<b>Cracked concrete, static and quasi-static action, working life 50 and 100 years</b>								
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	[mm [N/mm <sup>2</sup> ]]	0,071	0,072	0,074	0,076	0,079	0,082
	$\delta_{N\infty}$ - factor		0,115	0,122	0,128	0,135	0,142	0,171
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,095	0,096	0,099	0,102	0,106	0,110
	$\delta_{N\infty}$ - factor		0,154	0,163	0,172	0,181	0,189	0,229
<b>Diamond drilling</b>								
<b>Uncracked concrete, static and quasi-static action, working life 50 years</b>								
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	[mm [N/mm <sup>2</sup> ]]	0,012	0,012	0,013	0,014	0,014	0,015
	$\delta_{N\infty}$ - factor		0,019	0,019	0,020	0,022	0,023	0,025
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,014	0,014	0,015	0,016	0,016	0,018
	$\delta_{N\infty}$ - factor		0,053	0,055	0,058	0,062	0,065	0,070
<b>Cracked concrete, static and quasi-static action, working life 100 years</b>								
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	[mm [N/mm <sup>2</sup> ]]	0,012	0,012	0,013	0,014	0,014	0,015
	$\delta_{N\infty}$ - factor		0,021	0,021	0,023	0,024	0,025	0,027
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,014	0,014	0,015	0,016	0,016	0,018
	$\delta_{N\infty}$ - factor		0,039	0,040	0,043	0,045	0,047	0,051

<sup>1)</sup> Calculation of the displacement

$$\delta_{N0} = \delta_{N0}\text{- factor} \cdot \tau; \quad \tau: \text{acting bond stress under tension load}$$

$$\delta_{N\infty} = \delta_{N\infty}\text{- factor} \cdot \tau;$$

**Table C23: Displacement factors<sup>1)</sup> under shear load: internally threaded anchor rod**

Internally threaded anchor rod		VMU-IG M 6	VMU-IG M 8	VMU-IG M 10	VMU-IG M 12	VMU-IG M 16	VMU-IG M 20	
<b>Uncracked and cracked concrete, static and quasi-static action</b>								
All temperature ranges	$\delta_{V0}$ - factor	[mm/(kN)]	0,07	0,06	0,06	0,05	0,04	0,04
	$\delta_{V\infty}$ - factor		0,10	0,09	0,08	0,08	0,06	0,06

<sup>1)</sup> Calculation of the displacement

$$\delta_{V0} = \delta_{V0}\text{- factor} \cdot V; \quad V: \text{acting shear load}$$

$$\delta_{V\infty} = \delta_{V\infty}\text{- factor} \cdot V;$$

**Injection System VME plus**

**Performance**  
Displacements (internally threaded anchor rod)

**Annex C20**

**Table C24: Displacement factors<sup>1)</sup> under tension load (rebar)**

Reinforcing bar		Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 24	Ø 25	Ø 28	Ø 32	
<b>Hammer-, compressed air or vacuum drilling</b>												
<b>Uncracked concrete, static and quasi-static action, working life 50 and 100 years</b>												
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	$\left[ \frac{\text{mm}}{[\text{N}/\text{mm}^2]} \right]$	0,028	0,029	0,030	0,031	0,033	0,035	0,038	0,038	0,040	0,043
	$\delta_{N\infty}$ - factor		0,015	0,015	0,016	0,017	0,017	0,019	0,020	0,020	0,021	0,023
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,038	0,039	0,040	0,042	0,044	0,047	0,051	0,051	0,054	0,058
	$\delta_{N\infty}$ - factor		0,047	0,049	0,051	0,053	0,055	0,059	0,065	0,065	0,068	0,072
<b>Cracked concrete, static and quasi-static action, working life 50 and 100 years</b>												
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	$\left[ \frac{\text{mm}}{[\text{N}/\text{mm}^2]} \right]$	0,069	0,071	0,072	0,073	0,074	0,076	0,079	0,079	0,081	0,084
	$\delta_{N\infty}$ - factor		0,115	0,122	0,128	0,135	0,142	0,155	0,171	0,171	0,181	0,194
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,092	0,095	0,096	0,098	0,099	0,102	0,106	0,106	0,109	0,113
	$\delta_{N\infty}$ - factor		0,154	0,163	0,172	0,181	0,189	0,207	0,229	0,229	0,242	0,260
<b>Diamond drilling</b>												
<b>Uncracked concrete, static and quasi-static action, working life 50 years</b>												
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	$\left[ \frac{\text{mm}}{[\text{N}/\text{mm}^2]} \right]$	0,008	0,009	0,009	0,010	0,011	0,012	0,013	0,013	0,014	0,015
	$\delta_{N\infty}$ - factor		0,018	0,018	0,019	0,020	0,021	0,024	0,027	0,027	0,028	0,031
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,009	0,011	0,011	0,012	0,013	0,014	0,015	0,015	0,016	0,018
	$\delta_{N\infty}$ - factor		0,048	0,051	0,054	0,058	0,061	0,068	0,076	0,076	0,081	0,088
<b>Uncracked concrete, static and quasi-static action, working life 100 years</b>												
Temperature range I: 40°C / 24°C	$\delta_{N0}$ - factor	$\left[ \frac{\text{mm}}{[\text{N}/\text{mm}^2]} \right]$	0,008	0,009	0,009	0,010	0,011	0,012	0,013	0,013	0,014	0,015
	$\delta_{N\infty}$ - factor		0,018	0,020	0,021	0,022	0,024	0,026	0,029	0,029	0,031	0,034
Temperature range II: 72°C / 50°C	$\delta_{N0}$ - factor		0,009	0,011	0,011	0,012	0,013	0,014	0,015	0,015	0,016	0,018
	$\delta_{N\infty}$ - factor		0,035	0,037	0,040	0,042	0,045	0,049	0,055	0,055	0,059	0,064

<sup>1)</sup> Calculation of the displacement

$$\delta_{N0} = \delta_{N0}\text{- factor} \cdot \tau; \quad \tau: \text{acting bond stress under tension load}$$

$$\delta_{N\infty} = \delta_{N\infty}\text{- factor} \cdot \tau;$$

**Table C25: Displacement factors<sup>1)</sup> under shear load (rebar)**

Reinforcing bar		Ø 8	Ø 10	Ø 12	Ø 14	Ø 16	Ø 20	Ø 24	Ø 25	Ø 28	Ø 32	
<b>Uncracked and cracked concrete, static and quasi-static action</b>												
All temperature ranges	$\delta_{V0}$ - factor	$[\text{mm}/(\text{kN})]$	0,06	0,05	0,05	0,04	0,04	0,04	0,03	0,03	0,03	0,03
	$\delta_{V\infty}$ - factor		0,09	0,08	0,08	0,06	0,06	0,05	0,05	0,05	0,04	0,04

<sup>1)</sup> Calculation of the displacement

$$\delta_{V0} = \delta_{V0}\text{- factor} \cdot V; \quad V: \text{acting shear load}$$

$$\delta_{V\infty} = \delta_{V\infty}\text{- factor} \cdot V;$$

**Injection System VME plus**

Performance  
Displacements (rebar)

**Annex C21**